

Chemical vapor deposition of tungsten-based layers on detonation coatings

Evgeny Ruban

evgeny.ruban991@gmail.com

Frumkin Institute of Physical Chemistry and Electrochemistry Russian Academy of Sciences

Sergey Vashin

Frumkin Institute of Physical Chemistry and Electrochemistry Russian Academy of Sciences

Stepan Rachko

Frumkin Institute of Physical Chemistry and Electrochemistry Russian Academy of Sciences

Sergey Rybakov

Frumkin Institute of Physical Chemistry and Electrochemistry Russian Academy of Sciences

Research Article

Keywords: detonation spraying coatings, chemical vapor deposition, tungsten coating, tungsten hexafluoride WF₆

Posted Date: October 19th, 2026

DOI: <https://doi.org/10.21203/rs.3.rs-11244194/v1>

License: © ⓘ This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

Additional Declarations: No competing interests reported.

Chemical vapor deposition of tungsten-based layers on detonation coatings

Evgeny Ruban*, Sergey Vashin, Stepan Rachko, Sergey Rybakov

*Frumkin Institute of Physical Chemistry and Electrochemistry Russian
Academy of Sciences, 31-4, Leninsky prospect, 119071 Moscow, Russia.*

*Corresponding author, e-mail: evgeny.ruban991@gmail.com

Received XX.XX.2026

Abstract

In this study, detonation coatings were preapplied as adhesive intermediate layers obtained from WC-Co, WC-Ni(10), WC-Ni(20), WC-Co-Cr and NiCr-Cr₃C₂ powders. Tungsten hexafluoride WF₆ is used for chemical vapor deposition of tungsten coatings. The dispersed composition of the powders was studied via laser diffraction, the phase composition of the powders and coatings obtained from them via X-ray diffraction, and chemical element analysis via EDS. The powder shape and the “detonation coating/tungsten coating” and “detonation coating/substrate” interfaces were examined by scanning electron microscopy. The combined use of detonation spraying and chemical vapor deposition allows the distributed deposition of tungsten coatings on a steel substrate from the detonation coating sublayer and regulates the porosity of the surface of detonation coatings by depositing a layer of tungsten on them via chemical vapor deposition.

Keywords: detonation spraying coatings, chemical vapor deposition, tungsten coating, tungsten hexafluoride WF₆

Introduction

The general causes of failure of industrial equipment components and parts are friction and abrasive types of wear [1]. Various types of surface treatment are used to increase wear resistance: chemical and thermal treatment [2], thermal spraying coatings (HVOF, HVOF, laser cladding, and plasma spraying), physical vapor deposition (PVD) (magnetron, ion and vacuum types of deposition), chemical vapor deposition (CVD), laser melting, arc deposition, and galvanic coatings, as well as hardness and superhard alloys, and the introduction of special alloying additives into their composition (tungsten, molybdenum, chromium, ceramic species, etc.) [3-5].

35 A flexible approach is to use hardness wear-resistant coatings, which are available via
36 a limited number of methods. Chromium-based hardness galvanic coatings are good examples
37 for wear-resistant applications [6], but the high degree of toxicity of the chrome plating
38 process limits their use [7]. The hardness of compound layers produced via physical vapour
39 deposition methods is difficult to obtain with equal compositions and thicknesses of complex
40 products [8]. Thermal spraying coatings are widely used [9], but they have high porosity,
41 which is unacceptable for most applications, and contain a multiphase structure, which
42 reduces their operational properties [10]. Tungsten-based CVD coatings, including tungsten
43 carbides [11, 12], cannot be directly deposited on steel surfaces [13].

44 Combining hardness coating technologies to obtain the best quality product for
45 industrial practical application is an extremely urgent task. The approach of depositing PVD
46 layers onto a WC-Co-system hard alloy substrate has already been applied [14-18].
47 Detonation-gaseous spraying (D-gun), which is one of the methods of thermal spraying,
48 allows the application of coatings that preserve the original phase-element composition of the
49 original powders, with good adhesion to the surface, uniformity and equal thickness without
50 surface heat treatment, including on internal surfaces (with some restrictions). The
51 combination of D-gun and CVD makes it possible to provide porosity closure via CVD layers
52 for D-gun coatings and, conversely, to provide adhesion contact CVD coatings for steel
53 subscribed underlayer D-gun coatings. This research is dedicated to matching the same layers.

54 55 Experimental

56 The detonation-gaseous spraying of metal and ceramic powders was implemented via
57 the D-gun automatic technologic complex ADU "Ob" (NTC Detonatsiya, Russia) [19].
58 Acetilene C_2H_2 (pure A, NII KM, Russia) was used as a gas fuel, and the oxidant was gaseous
59 oxygen O_2 (99.99%, NII KM, Russia). Sample surfaces were previously cleaned of dirt and
60 scale with activation immediately before being sprayed with quartz sand via air abrasive
61 treatment (species scale 0.5–1.5 mm) [20-22].

62 Tungsten layers were obtained via CVD in a vacuum reactor with a heat side with the
63 tungsten precursor tungsten hexafluoride WF_6 (99.99%, NPO Luch, Russia) and a reduction
64 in gaseous hydrogen H_2 (99.999 %, NII KM, Russia). Highly active chemical transformation
65 products were deactivated by spraying aqueous alkaline solution in a scrubber, which was
66 installed in series after the rotary vane vacuum pump [23].

67 Samples preparation (steels St3 or St45 20x30x3 mm³) were performed via a
68 metallographic cutting machine, MICRACUT 202 (Metkon, USA), with subsequent

69 production of a metallographic section on a pressing machine, ECOPRESS 52 (Metkon,
70 USA), and grinding and polishing on an automatic grinding and polishing machine,
71 FORCIPOL 102 (Metkon, USA).

72 The powders granulometric composition were measured on a particle size analyser via
73 a laser diffraction Mastersizer 2000 M (Malvern Instruments, GB) via an automatic liquid
74 dispersion and a sample feeding module Hydro 2000S [24-26]. Powder flowability and bulk
75 density were investigated via the weight method via a Hall funnel [27, 28].

76 The D-gun powders used were No. 1 – WC-Co(17) (Sulzer Metco, USA), No. 2 –
77 WC-Ni(10) (n/n, CPR), No. 3 – WC-Ni(20) (Technikord, Russia), No. 4 – WC-Co-Cr
78 (Gorizont pokritiy, Russia), and No. 5 – NiCr-Cr₃C₂ (HTC, CPR).

79 Powders morphology and particle size analysis were carried out on an ICOE
80 CB800PRT optical microscope (Synercon, Russia) in bright field mode [29-31]. The
81 microstructure and thickness of the coatings were investigated via a metallographic inverted
82 microscope (ICOE MIV5500D; Synercon, Russia) according to standard methods [32].

83 Powder and coating phase element analyses were performed via X-ray phase analysis
84 (XRD) on an X-ray diffractometer (Tongda TD-3700; Dandong Tongda, KHP) with CuK α
85 radiation. The results of the experiment were processed via QualX software.

86 Powder species and multilayer coating microstructures were investigated by scanning
87 electron microscopy (SEM) SM-32A (Melytec, CPR) with an X-ray detector Xplore 30
88 (Oxford Instruments, GB) for energy dispersive analysis (EDX) to study the elemental
89 chemical composition of the powders and coatings [33, 34]. The accumulation and processing
90 of X-ray spectra were performed with AZtecOne software.

91


92 **Results and discussion**

93 **Powders investigation**

94 The average bulk diameter of species and specific surface area for powder No. 1 are
95 43.62 μm and 0.162 m^2/g , respectively; No. 2, 49.78 μm and 0.254 m^2/g ; No. 3, 32.39 μm and
96 0.387 m^2/g ; No. 4, 32.42 μm and 0.197 m^2/g ; and No. 5, 38.76 μm and 0.168 m^2/g .

97 Powder No. 1 (Fig. 1,a) contains particles of an elongated shape that are close to
98 spherical. The particles of powder No. 1 mostly have a spherical shape of approximately the
99 same geometric dimensions; as a result of the particle spheroidization operation, no dust
100 fraction was detected. The single powder particles consisted of sintered polycrystals of
101 submicron size. Powder No. 2 (Fig. 1,b) contains species with predominantly spherical

102 shapes, and ultrafine particles of submicron sizes that do not participate in the coating
 103 spraying process burn when the detonation products are fired. Powder particle No. 2 has a
 104 spherical shape with no signs of agglomeration; the particles themselves consist of WC
 105 tungsten carbide crystals interconnected by nickel bonds. Owing to the application of the
 106 particle spheroidization operation, WC crystallites have rounded fused faces. Powder No. 3
 107 (Fig. 1,c) contains mainly particles of complex multifaceted shapes, as well as many ultrafine
 108 particles of submicron sizes. Powder particles No. 3 have arbitrary polyhedral shapes with
 109 geometric dimensions in a wide range. Apparently, the powder was not subjected to any
 110 postprocessing (screening, size concentration, spheroidization, etc.). Powder No. 4 (Fig. 1, d)
 111 consists mainly of spherical species with a low dust fraction. The particles of powder No. 4
 112 have a spherical shape, which is obtained as a result of the particle spheroidization operation,
 113 and have similar geometric dimensions. No dust fraction was detected. The single powder
 114 particles consisted of sintered polycrystals of submicron size. No. 5 (Fig. 1, e) is mainly
 115 represented by spherical species, and there are enlarged agglomerates of species. Powder No.
 116 5 is predominantly spherical in shape with agglomeration of smaller submicron particles with
 117 larger microscale sizes, and the surface of the powder species is represented by individual
 118 crystallites without sharp angles that are "fused" during spheroidization.

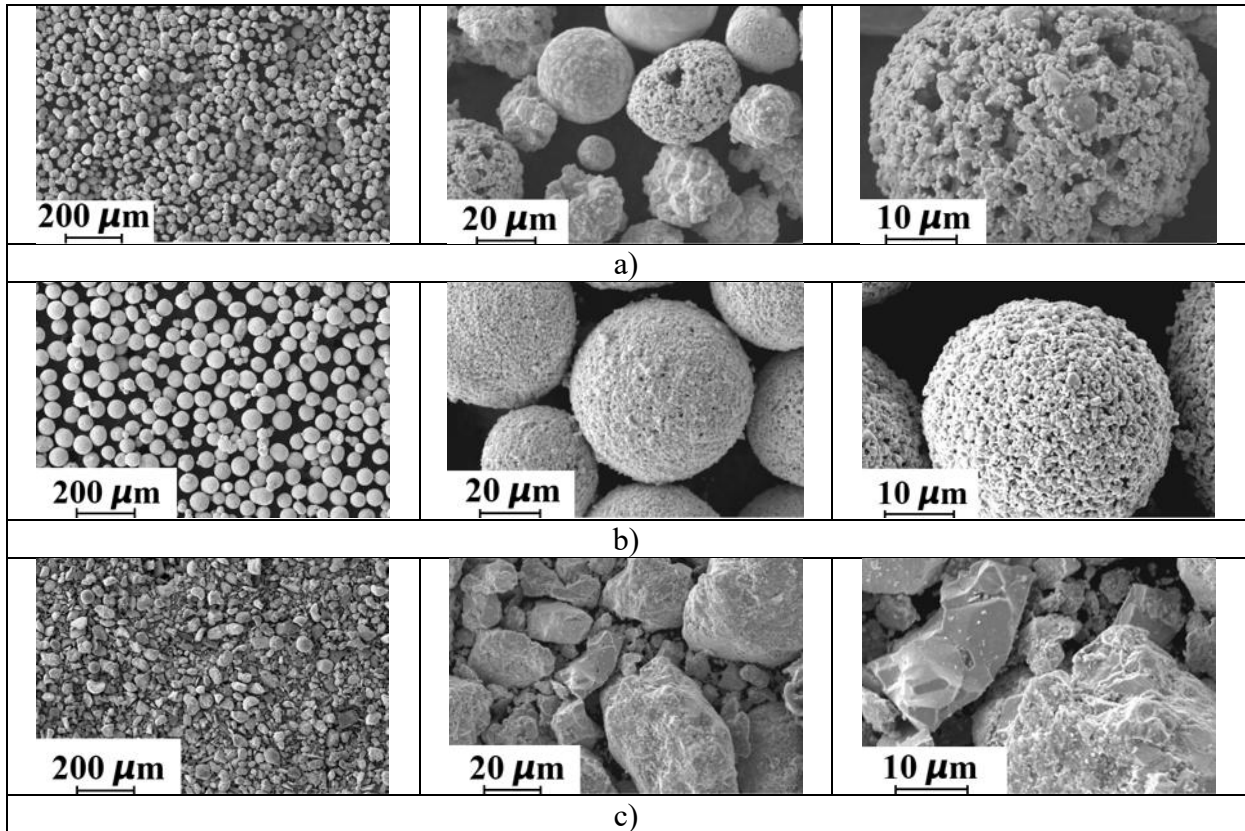

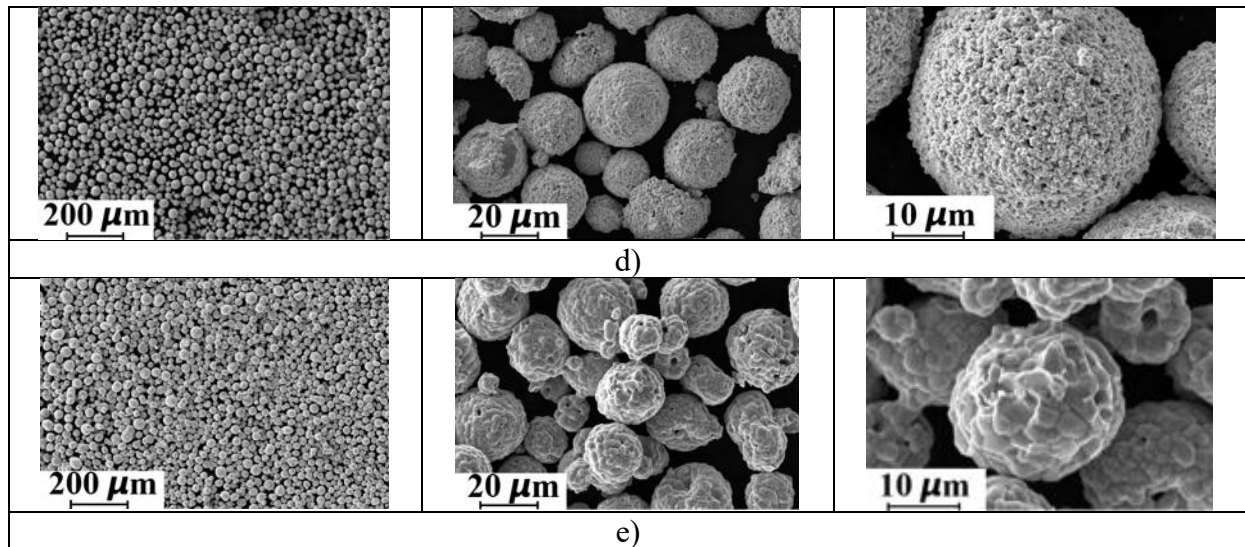
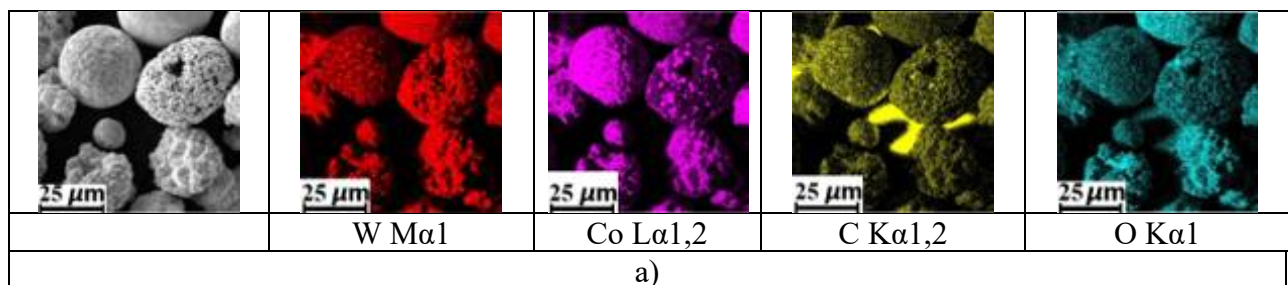


Fig. 1. SEM images of powder samples: a) No. 1, b) No. 2, c) No. 3, d) No. 4, e) No. 5

Powder No. 1 (Fig. 2a) consists of W, Co, C, O and Cr 65.93/23.17, 22.92/25.13, 6.10/32.79, 4.51/18.23 and 0.55/0.68 wt.%/at.%, respectively. Powder No. 2 (Fig. 2,b) consists of W, C and Ni at 82.36/23.59, 9.45/57.26 and 8.18/10.14 wt.%/at.%, respectively. Powder No. 3 (Fig. 2,c) contains W, Ni, C, Cr, O, Fe and Co 45.37/12.50, 29.31/25.30, 9.49/40.03, 6.11/5.95, 3.34/10.58, 3.25/2.95 and 3.14/2.70 wt.%/at.%, respectively. The presence of Fe, Co, Cr and O impurities in the powder composition indicates the ingress of materials from the lining of pipelines and assemblies of technological machines, most likely represented by stainless steels containing these elements, during the powder production process owing to the higher hardness of the phases in the processed powder materials and their dry abrasive action, as well as the absence or insufficient organization of quality control of manufactured powder products. Powder No. 4 (Fig. 2, d) consists of W, C, Co, O and Cr at 79.00/26.99, 10.63/55.58, 6.22/6.62, 2.13/8.36 and 2.02/2.44 wt.%/at.%, respectively. Powder №5 (Fig. 2e) consists of Cr, C, Ni and W at 76.17/49.93, 16.30/46.24, 6.16/3.58 and 1.37/0.25 wt.%/at.%, respectively.



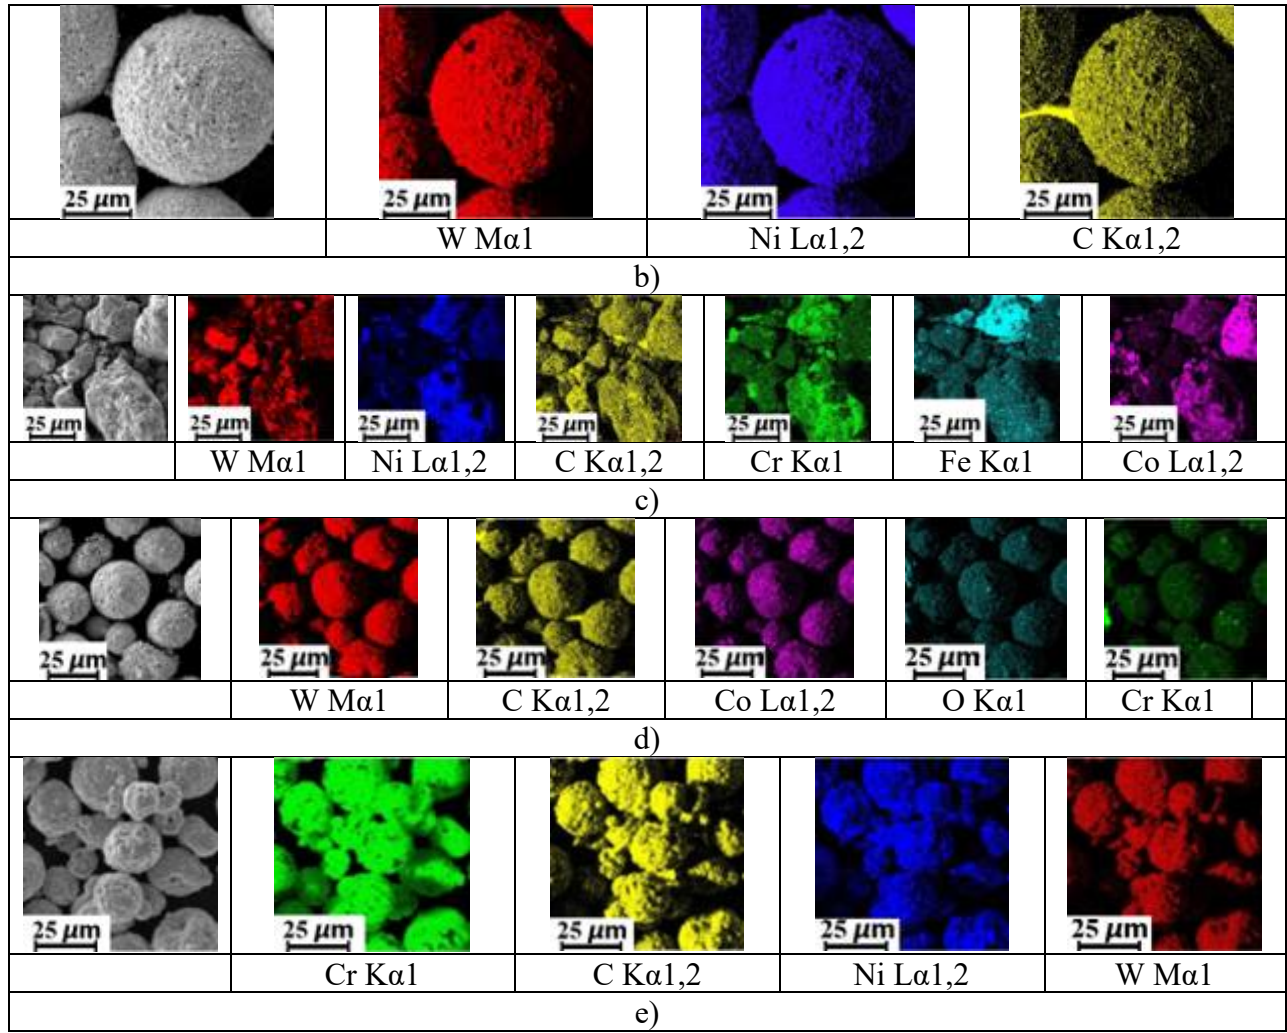


Fig. 2. Distribution of elements over the surface of powder particles: a) No. 1, b) No. 2, c) No. 3, d) No. 4, e) No. 5

Detonation- gaseous spraying coatings

The detonation coatings produced by spraying technology are shown in Table 1.

Table. 1. D-gun coating spraying technique


No.	Composition	L , mm	FF , %	O_2/C_2H_2	h , μm	v , mm/min
1	WC-Co(17)	150	48	1.08	5	2000
2	WC-Co-Cr	150	48	1.07	5	2000
3	NiCr-Cr ₃ C ₂	160	27	1.1	5.5	1800
4	WC-Ni(10)	150	47	1.08	6	2100
5	WC-Ni(20)	160	45	1.08	5.5	2000

L – distance from the trunk section to the sprayed plane, mm; FF – barrel fill factor, %;

h – thickness of a single layer, μm ; v – speed of movement of the manipulator, mm/min.

Coating No. 1 (Fig. 3a) is characterized by a dense uniform microstructure with an observed regular microporosity. The “coating/substrate” interface border has no peeling throughout, which indicates sufficient coating adhesion on the surface. Coating No. 2 (Fig. 3,

144 b) is characterized by a porous microstructure with the possibility of forming pores according
 145 to its coating bulk in the presence of satisfactory coating adhesion on the substrate surface, as
 146 expressed by the absence of peeling of the coating sections. Coating No. 3 (Fig. 3,c) has a
 147 dense, homogeneous microstructure with a minimum number of micron-scale pores. The
 148 “coating/substrate” interface border has distinct halos with the possibility of forming “shells”
 149 that do not noticeably affect the adhesion of the sprating layer. In coating No. 4 (Fig. 3, d),
 150 irregular cracks are observed, which in turn do not lead to deterioration of coating adhesion or
 151 detachment. The coating microstructure is quite homogeneous, with the possibility of the
 152 appearance of closed pores at the micron scale in the near-surface coating layer. Coating No.
 153 5 (Fig. 3e) has a “loose” microstructure with the possibility of forming an open, branched
 154 porosity on the coating bulk. The “coating/substrate” interface border has no signs of peeling.

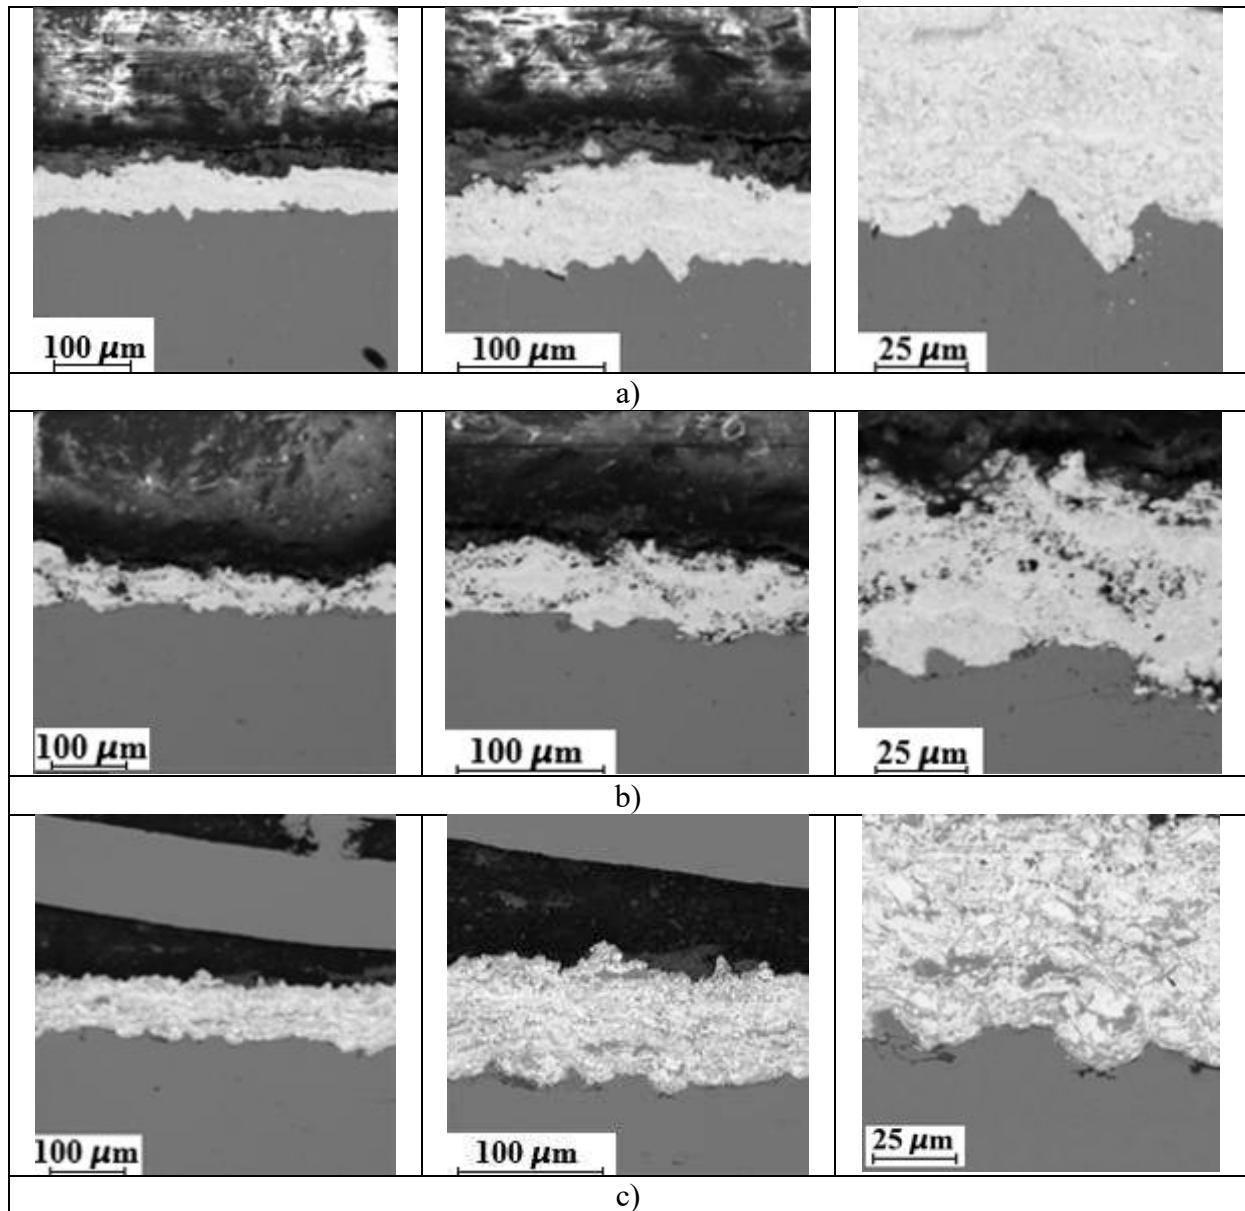

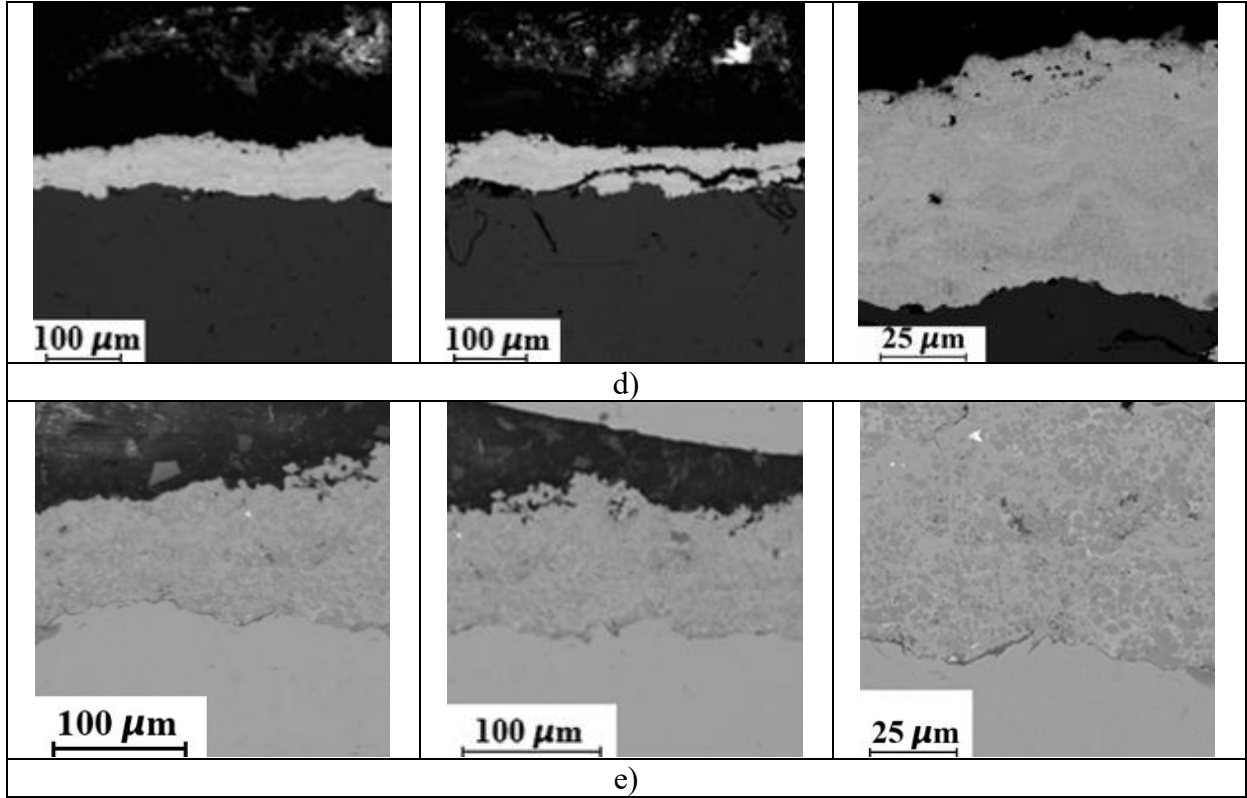


Fig. 3. SEM images of D-gun coatings: a) No. 1, b) No. 2, c) No. 3, d) No. 4, e) No. 5

Coating No. 1 (Fig. 4a) containing phases of WC and Co, which are contained in the initial powder, and α -W results in dissociated tungsten carbide (WC) during D-gun spraying. Coating No. 2 (Fig. 4,b) contains phases of WC and Ni, which are present in the original powder, and W_2C and W result in the dissociation of tungsten carbide WC during D-gun spraying. Coating No. 3 (Fig. 4,c) contains phases of WC and Ni, which are contained in the initial powder, and W_2C , W results in dissociated tungsten carbide (WC) during D-gun spraying. Coating No. 4 (Fig. 4, d) contains phases of WC and Co, which are contained in the initial powder, and W_2C results in the dissociation of tungsten carbide WC during D-gun spraying. The Cr phase, which is present in the original powder, was not detected in the coating; most likely, chromium partially burned out at low temperatures, and its small amount in the spraying coating could not be detected by XRD because of the detection limit of the compounds by a diffractometer. Coating No. 5 (Fig. 4e) contains the phases Cr, NiCr and Ni, which are contained in the initial powder, as well as Cr_3C_2 and Cr_2O_3 , which are formed during spraying coating.

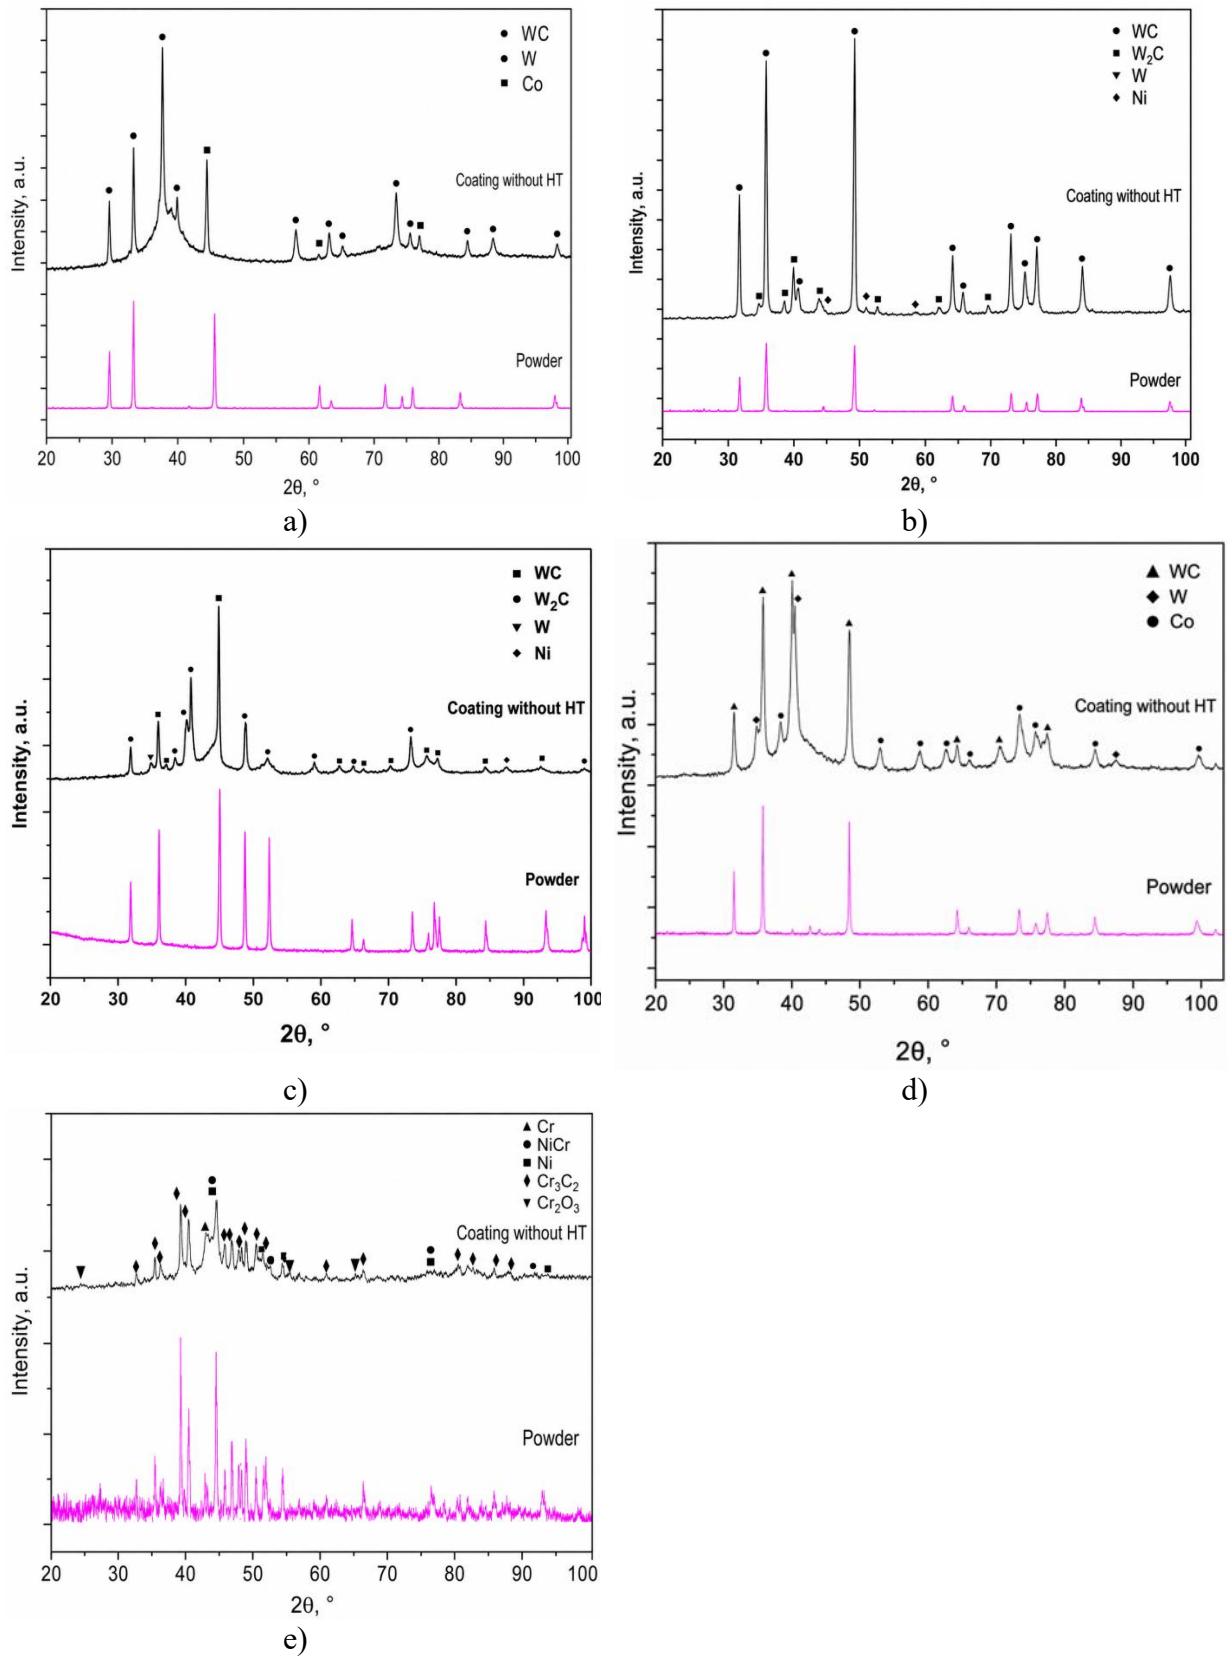



Fig. 4. Powders and D-gun coatings diffractograms: a) No. 1, b) No. 2, c) No. 3, d) No. 4,

e) No. 5

CVD tungsten coatings

173 CVD tungsten coatings were obtained via the following methods: 1 l/h WF_6 , 5.5 l/h
 174 H_2 , a precipitation temperature of 530 °C, a pressure of 180 ± 10 Torr, and precipitation for
 175 40 min.

176 The two-layer WC-Co coating with deposited tungsten has a uniform microstructure,
 177 the "substrate-detonation coating" boundary is clearly visible, and the "detonation coating-
 178 CVD coating" boundary is distinguishable by the presence of a denser outer CVD layer of
 179 tungsten. Submicron-sized pores are also discernible in the detonation layer. The
 180 microstructure of the detonation layer contains some porosity with submicron–micron
 181 dimensions (Fig. 4a). Two-layer WC–Ni(10) coatings with deposited tungsten have a uniform
 182 phase distribution in the detonation layer, and the boundaries of the layers are distinguishable.
 183 The closure of the surface porosity in the detonation layer by the deposited CVD layer of
 184 tungsten is also noticeable (Fig. 4,b). The two-layer WC–Ni(20) coating with deposited
 185 tungsten has distinguishable "substrate-detonation coating" and "detonation coating-CVD
 186 coating" boundaries, and no porosity was visually detected in the coating layers (Fig. 4,c).
 187 The two-layer WC–Co–Cr coating with deposited tungsten has a clear "substrate-detonation
 188 coating" boundary, and the CVD layer of tungsten on the detonation layer has a small
 189 thickness and is distinguishable on the outer surface of the sample because of the denser
 190 microstructure of tungsten (Fig. 4,d). The two-layer NiCr– Cr_3C_2 coating with deposited
 191 tungsten has a clearly distinguishable boundary "substrate-detonation coating" and
 192 "detonation coating-CVD coating" (Fig. 4e).

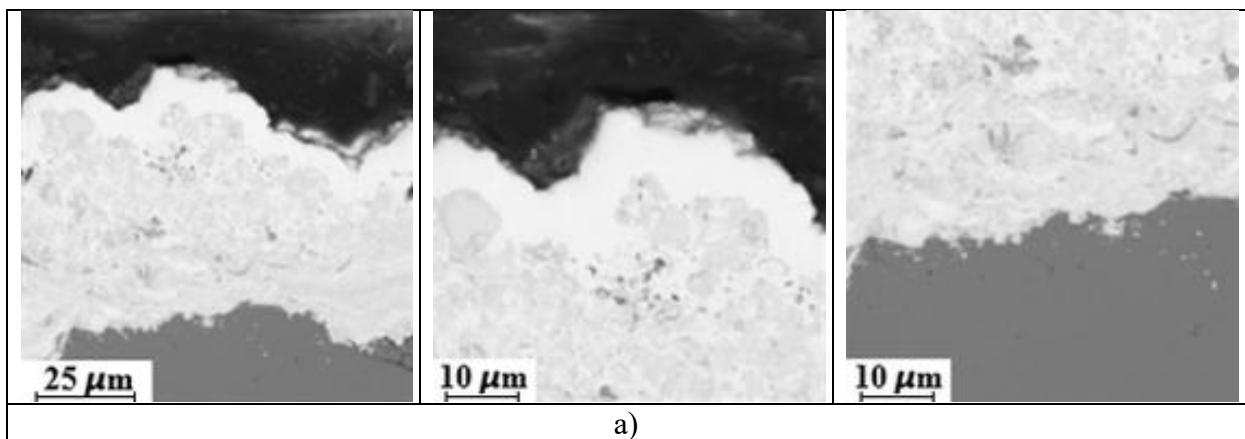

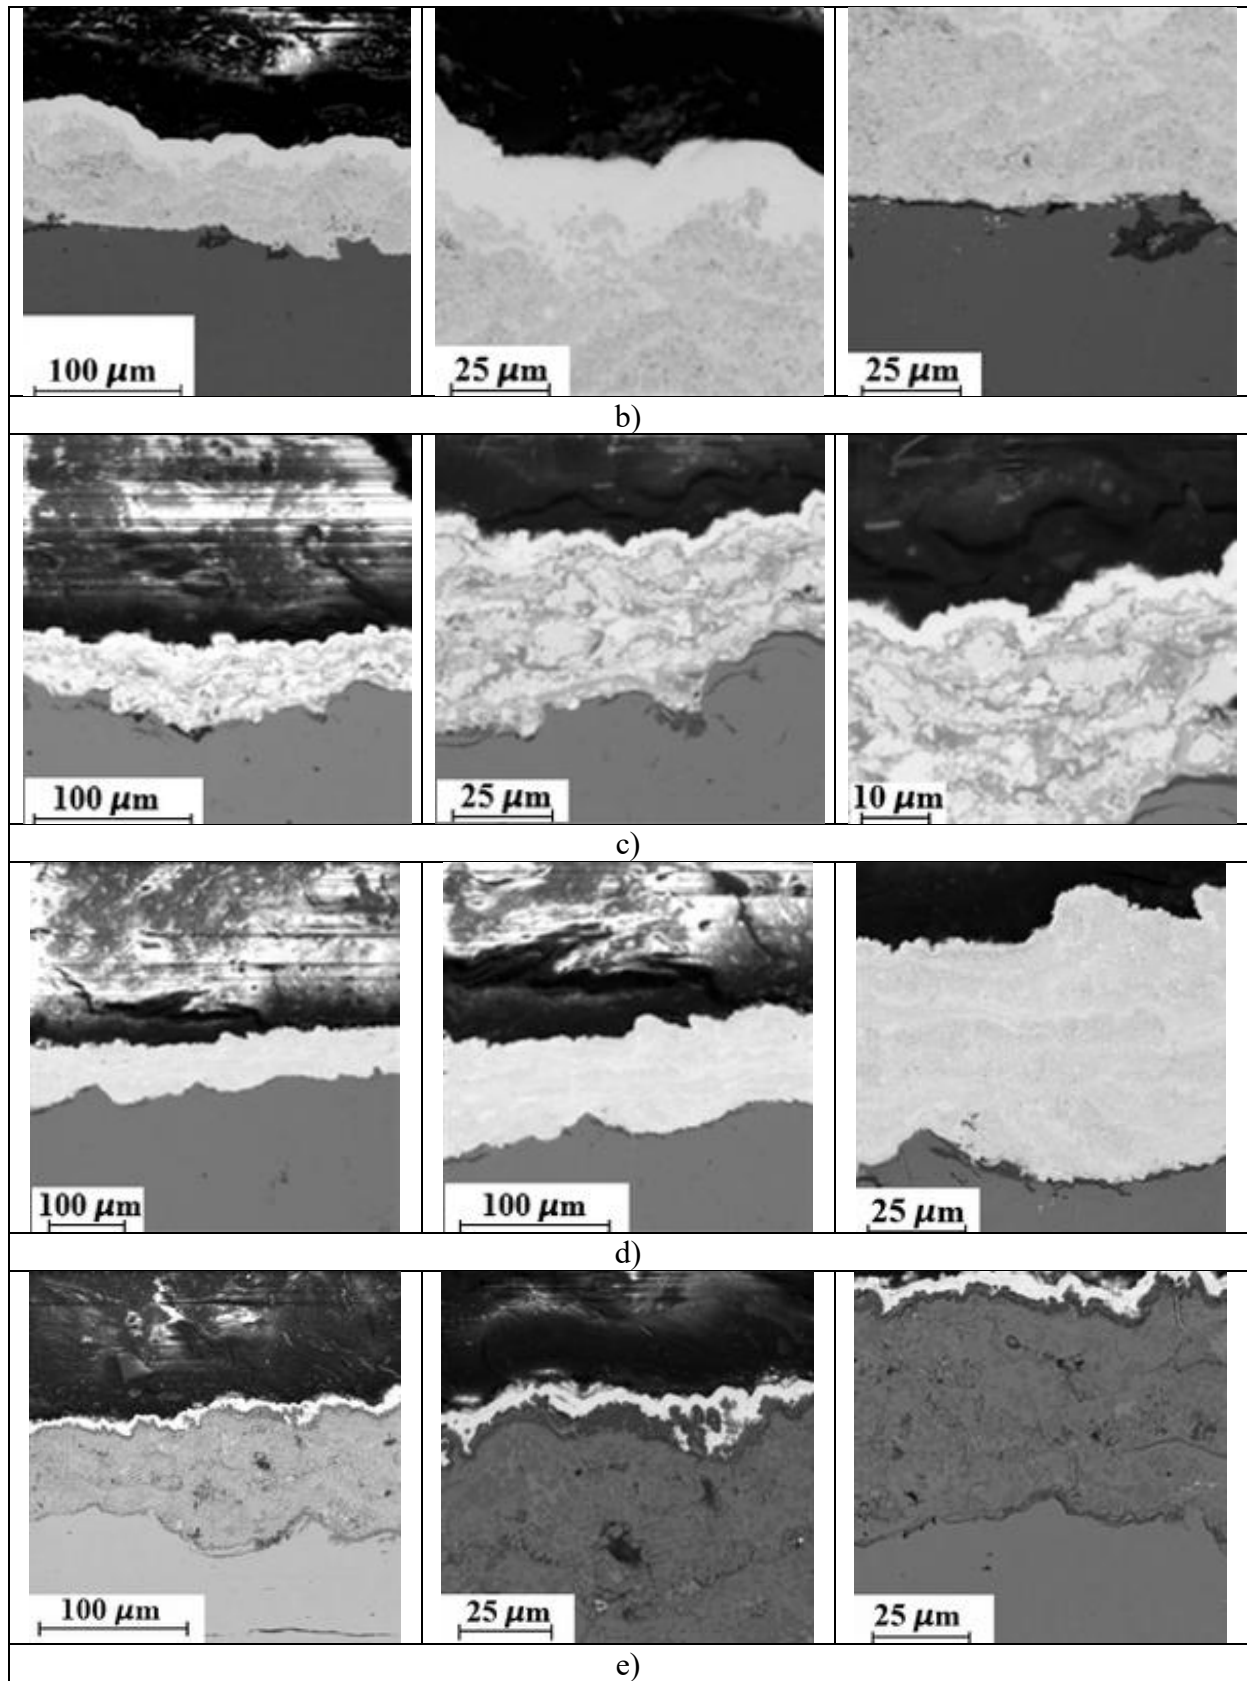
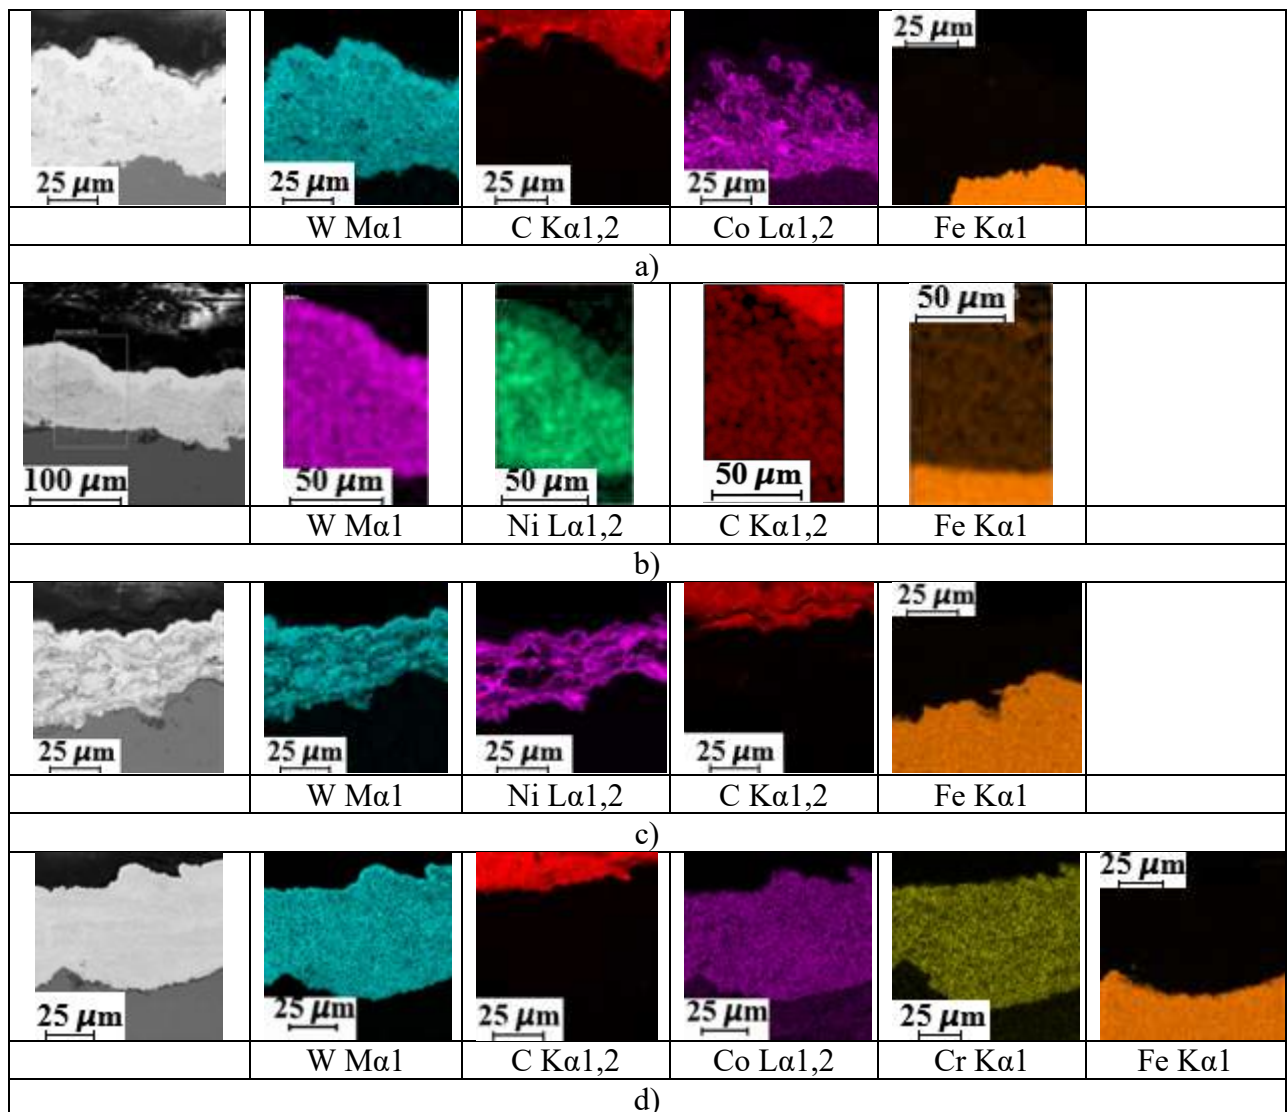


Fig. 5. SEM images of D-gun coatings with deposited W coatings: a) WC-Co/W, b) WC-Ni(10)/W, c) WC-Ni(20)/W, d) WC-Co-Cr/W, e) NiCr-Cr₃C₂/W

195 The two-layer WC-Co/W coating contains W with a uniform thickness distribution,
 196 and Co is less evenly distributed: the concentration decreases slightly towards the sample
 197 surface, and carbon in the D-gun layer is poorly expressed owing to its identification features.
 198 The outer CVD layer of tungsten is distinguishable on the surface of the sample (Fig. 5a). The
 199 WC-Ni(10)/W coating consists of W, Ni and C with a uniform thickness distribution. The
 200 outer CVD layer of tungsten is distinguishable on the surface of the sample (Fig. 5,b). The
 201 WC-Ni(20)/W coating consists of W, Ni and C with a uniform thickness distribution. The
 202 outer CVD layer of tungsten is distinguishable on the surface of the sample (Fig. 5,c). The
 203 WC-Co-Cr/W coating contains W, Co, and Cr with a uniform thickness distribution; carbon
 204 in the D-gun layer is poorly expressed because of its identification features. The outer CVD
 205 layer of tungsten is distinguishable on the surface of the sample (Fig. 5,d). The NiCr-Cr₃C₂/W
 206 coating contains Ni, C and Cr with a uniform thickness distribution. The outer CVD layer of
 207 tungsten is clearly visible on the surface of the sample (Fig. 5,e).



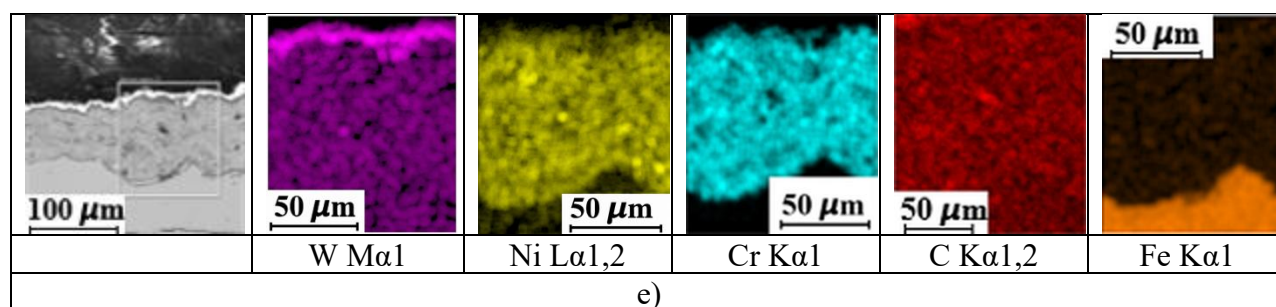


Fig. 6. Distribution of elements on various metallographic detonation coatings and deposition of CVD layers of tungsten on a) WC-Co/W, b) WC-Ni(10)/W, c) WC-Ni(20)/W, d) WC-Co-Cr/W, e) NiCr-Cr₃C₂/W

Conclusions

The chemical vapour deposition of a tungsten coating from tungsten hexafluoride WF_6 onto detonation coatings composed of WC-Co, WC-Ni(10), WC-Ni(20), WC-Co-Cr and NiCr-Cr₃C₂ sprayed onto a steel substrate was considered. Owing to the lack of adhesion between WF_6 CVD coatings and steel surfaces, detonation coatings can act as intermediate adhesive support layers on which tungsten CVD coatings can be obtained. This was confirmed by SEM, XRD, and EDS analyses of the obtained two-layer coating systems. The "substrate-detonation coating" and "detonation coating-tungsten coating" interfaces clearly have distinguishable boundaries. Notably, owing to the porosity of the detonation coatings resulting from the spraying process, it is possible to close part of the surface porosity by depositing a tungsten CVD coating. This effect of decreasing the porosity of CVD detonation coatings with a tungsten coating can be used to increase the corrosion resistance and wear resistance of coated parts and to obtain a smoother surface morphology without the need for rough machining.

Funding: This work was supported by the Ministry of Science and Higher Education of the Russian Federation (No. 075-15-2025-583).

Declarations

Conflict of interest The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

References

1. A. Patnaik, T. Singh, and V. Kukshal (2021) Tribology in Materials and Manufacturing: Wear, Friction and Lubrication, BoD—Books on Demand, Norderstedt, 333 p. ISBN-13: 978-1838805579.
2. H. Li, J. Chen, W. Zhang, H. Zhan, C. He, Z. Yang, H. Peng, and L. Leng (2023) Machine-Learning-Aided Thermochemical Treatment of Biomass: A Review, *Biofuel Res. J.*, 10(1), 1786–1809. doi: 10.18331/BRJ2023.10.1.4
3. P. Sarvar and H. Firuz, *Hard Alloy Applications* (2023), *Universum: Tekhnicheskie Nauki*, 8-4(113), 4–7 (in Russian). doi: 10.32743/UniTech.2023.113.8.15860
4. V. Kanyanta (2016) Hard, Superhard and Ultrahard Materials: An Overview, in *Microstructure-Property Correlations for Hard, Superhard, and Ultrahard Materials*, Springer, Cham, 1–23. doi: 10.1007/978-3-319-29291-5_1
5. Y. Wang, C. Feng, T. Lin, R. Zhu, J. Zhang, H. Yang, S. Yi, J. He, M. Tu, and G. Wei (2025) A Review of Wear-Resistant Coatings for Steel Substrates: Applications and Challenges, *Metals*, 15(11), 1231. doi: 10.3390/met15111231
6. N.V. Mandich and D.L. Snyder (2010) Electrodeposition of Chromium, in *Modern Electroplating*, 5th ed., M. Schlesinger and M. Paunovic, Eds., Wiley, Hoboken, NJ, 205–241. doi: 10.1002/9780470602638.ch12
7. S. Wang, C. Ma, and F.C. Walsh (2020) Alternative Tribological Coatings to Electrodeposited Hard Chromium: A Critical Review, *Trans. IMF*, 98(4), 173–185. doi: 10.1080/00202967.2020.1776962
8. B. Navinšek, P. Panjan, and I. Milošev (1999) PVD Coatings as an Environmentally Clean Alternative to Electroplating and Electroless Processes, *Surf. Coat. Technol.*, 116–119, 476–487. doi: 10.1016/S0257-8972(99)00145-0
9. Anon., Thermal Spray Service Market, Global Market Insights, <https://www.gminsights.com/industry-analysis/thermal-spray-service-market>. Accessed 4 April 2026.
10. H. Fukanuma (1994) A Porosity Formation and Flattening Model of an Impinging Molten Particle in Thermal Spray Coatings, *J. Therm. Spray Technol.*, 3(1), 33–44. doi: 10.1007/BF02648997
11. V.V. Dushik, N.V. Rozhanskii, V.O. Lifshits, T.V. Rybkina, and V.P. Kuzmin (2018) The Formation of Tungsten and Tungsten Carbides by CVD Synthesis and the Proposed Mechanism of Chemical Transformations and Crystallization Processes, *Mater. Lett.*, 228, 164–167. doi: 10.1016/j.matlet.2018.06.003

- 270 12. H. Zhang, X. Yu, Z. Nie, C. Tan, F. Wang, H. Cai, Y. Li, F. Wang, and H. Cai (2018)
 271 Microstructure and Growth Mechanism of Tungsten Carbide Coatings by Atmospheric CVD,
 272 Surf. Coat. Technol., 344, 85–92. doi: 10.1016/j.surfcoat.2018.03.023
- 273 13. E.A. Ruban and S.Yu. Rachko (2026) Thermodynamic Calculation of the Interaction of
 274 the Components of a Gaseous Medium with the Substrate Surface During CVD of Tungsten-
 275 Based Coatings, Russian Journal of Physical Chemistry A, 100 (10), 2247–2252. doi:
 276 10.1134/S0036024426701700
- 277 14. F.F. Komarov, V.M. Konstantinov, A.V. Kovalchuk, S.V. Konstantinov, and H.A.
 278 Tkachenko (2016) The Effect of Steel Substrate Prehardening on Structural, Mechanical, and
 279 Tribological Properties of Magnetron Sputtered TiN and TiAlN Coatings, Wear, 352–353,
 280 92–101. doi: 10.1016/j.wear.2016.02.008
- 281 15. H.G. Prengel, P.C. Jindal, K.H. Wendt, A.T. Santhanam, P.L. Hegde, and R.M. Penich
 282 (2001) A New Class of High Performance PVD Coatings for Carbide Cutting Tools, Surf.
 283 Coat. Technol., 139(1), 25–34. doi: 10.1016/S0257-8972(00)01080-X
- 284 16. A. Inspektor and P.A. Salvador (2014) Architecture of PVD Coatings for Metalcutting
 285 Applications: A Review, Surf. Coat. Technol., 257, 138–153. doi:
 286 10.1016/j.surfcoat.2014.08.068
- 287 17. Y. Long, J. Zeng, D. Yu, and S. Wu (2014) Microstructure of TiAlN and CrAlN Coatings
 288 and Cutting Performance of Coated Silicon Nitride Inserts in Cast Iron Turning, Ceram. Int.,
 289 40(7), 9889–9894. doi: 10.1016/j.ceramint.2014.02.083
- 290 18 B.M. de Freitas, D.S.L. Weiss, L.S. Santos, P. Soares, F.L. Amorim, J.M.F.P. Junior,
 291 C.A.H. Laurindo, and R.D. Torres (2025) Influence of Cobalt Content on the Adhesion of
 292 TiAlN and AlTiN/TiSiN Coatings on WC-Co Substrates, Surf. Interfaces, 72, 107339. doi:
 293 10.1016/j.surfin.2025.107339
- 294 19. T.P. Gavrilenko, A.L. Kiryakin, Yu.A. Nikolaev, and V.Yu. Ulyanitskii (2006)
 295 Automated Detonation Complex “Ob” for Powder Coating Deposition, STA (Sovremennyye
 296 Tekhnologii Avtomatizatsii), 4, 47–52 (in Russian).
- 297 20. Y.S. Borisov and Y.A. Kharlamov (1987) Thermal Spray Coatings from Powder
 298 Materials, Naukova Dumka, Kyiv, 210 p. (in Russian).
- 299 21. P.A. Vityaz, V.S. Ivashko, and E.D. Manuilov (1993) Theory and Practice of Flame
 300 Spraying, Navuka i Tekhnika, Minsk, 295 p. (in Russian). ISBN 5-343-01004-9.
- 301 22. V.V. Kudinov and V.M. Ivanov (1981) Plasma Deposition of Refractory Coatings,
 302 Mashinostroenie, Moscow, 192 p. (in Russian).

- 303 23. V.V. Dushik, E.A. Ruban, A.B. Drovosekov, A.A. Shaporenkov, and N.V. Rozhanskiy
 304 (2023) Synergetic Effect in Ni–P–W and W–C Multilayer Coating Systems Obtained by
 305 Chemical-Catalytic Metallization and Chemical-Vapor Deposition, *J. Surf. Investig.: X-ray*
 306 *Synchrotron Neutron Tech.*, 17(6), 1364–1371. doi: 10.1134/S1027451023060265
- 307 24. GOST R 8.777-2011 (2011) State System for Ensuring the Uniformity of Measurements.
 308 Disperse Composition of Aerosols and Suspensions. Determination of Particle Size by Laser
 309 Diffraction, Standartinform, Moscow. (in Russian).
- 310 25. ISO 13320:2020 (2020) Particle Size Analysis -- Laser Diffraction Methods, International
 311 Organization for Standardization, Geneva.
- 312 26. ISO 21501-1:2025 (2025) Determination of Particle Size Distribution—Single Particle
 313 Light Interaction Methods—Part 1: Light Scattering Aerosol Spectrometer, International
 314 Organization for Standardization, Geneva.
- 315 27. GOST 20899-98 (1998) Metallic Powders. Determination of Flowability by Means of a
 316 Calibrated Funnel (Hall Flowmeter), Standartinform, Moscow. (in Russian).
- 317 28. GOST 19440-94 (1994) Metallic Powders. Determination of Apparent Density. Part 1:
 318 Funnel Method. Part 2: Scott Volumeter Method, Standartinform, Moscow. (in Russian).
- 319 29. GOST R 56169-2014 (2014) Optics and Optical Instruments. Operation Microscope.
 320 Requirements and Test Methods, Standartinform, Moscow. (in Russian).
- 321 30. GOST R ISO 17123-1-2011 (2011) State System for Ensuring the Uniformity of
 322 Measurements. Optics and Optical Instruments. Field Procedures for Testing Geodetic and
 323 Surveying Instruments. Part 1: Theory, Standartinform, Moscow. (in Russian).
- 324 31. ISO 9342-1:2023 (2023) Optics and Optical Instruments—Test Lenses for Calibration of
 325 Focimeters—Part 1: Reference Lenses for Focimeters Used for Measuring Spectacle Lenses,
 326 International Organization for Standardization, Geneva.
- 327 32. I. Novikov, V.S. Zolotarevskii, K.K. Portnoi, N.A. Belov, D.V. Livanov, S.V.
 328 Medvedeva, A.A. Aksenov, and Yu.V. Evseev (2009) *Physical Metallurgy: Textbook. Vol. II*,
 329 V.S. Zolotarevskii, Ed., MISiS Publishing House, Moscow, 528 p. (in Russian). ISBN 978-5-
 330 87623-247-2
- 331 33. K.F.J. Heinrich (1981) *Electron Beam X-Ray Microanalysis*, Van Nostrand Reinhold
 332 Company, New York, NY, 578. ISBN-10: 0442232861, ISBN-13: 978-0442232863
- 333 34. J.I. Goldstein, D.E. Newbury, P. Echlin, D.C. Joy, C. Fiori, and E. Lifshin (1984)
 334 *Scanning Electron Microscopy and X-Ray Microanalysis*, Mir, Moscow, 1, 303; 2, 351. (in
 335 Russian translation).