

Facile One-pot Synthesis of CuCN by Pulsed Laser Ablation in Nitrile Solvents and Mechanistic Studies using Quantum Chemical Calculations

Talshyn Begildayeva

Gyeongsang National University

Ahreum Ahn

Korea Institute of Science & Technology Information

Shreyanka Shankar Naik

Gyeongsang National University

Seung Jun Lee

Gyeongsang National University

Jayaraman Theerthagiri

Gyeongsang National University

Tae Ho Kim

Gyeongsang National University

Myong Yong Choi (✉ mychoi@gnu.ac.kr)

Gyeongsang National University

Research Article

Keywords: Pulsed laser ablation in liquid, CuCN, Organic nitriles, Binding energy, Quantum chemical calculations

Posted Date: February 16th, 2021

DOI: <https://doi.org/10.21203/rs.3.rs-200000/v1>

License: © ⓘ This work is licensed under a Creative Commons Attribution 4.0 International License.

[Read Full License](#)

Version of Record: A version of this preprint was published at Scientific Reports on July 13th, 2021. See the published version at <https://doi.org/10.1038/s41598-021-93768-7>.

Abstract

Binding energies of different nitrile solvents and their utilization for CuCN formation were investigated through quantum chemical calculations. A pulsed laser ablation in liquid (PLAL) method for CuCN synthesis was developed herein. Initially, the interaction between the pulsed laser and the Cu-target generated Cu-ions and electrons at the point of contact. The laser beam also exhibited sufficient energy to dissociate the bonds of the respective solvents. In the case of acetonitrile, the oxidized Cu-ions bonded with CN^- to produce CuCN with a cubic-structure. Other nitrile solvents generated spherically-shaped Cu@graphitic carbon (Cu@GC) nanoparticles. Thus, the production of CuCN was favorable only in acetonitrile due to the availability of the cyano-group immediately after the fragmentation of acetonitrile (CH_3^+ and CN^-) under PLAL. Conversely, propionitrile and butyronitrile released large amounts of hydrocarbons, which deposited on Cu NPs surface to form GC layers. Following the encapsulation of Cu NPs with carbon shells, further interaction with the cyano-group was not possible. Subsequently, theoretical study on the binding energies of nitrile solvents was confirmed by highly correlated basic sets of B3LYP and MP2 which results were consistent with the experimental outcomes. The findings obtained herein could be utilized for the development of novel metal–polymer materials.

1. Introduction

The production of metal cyanides has attracted considerable interest due to their commercial applications in different industries. For instance, CuCN and AgCN are employed in the fields of pharmacology, gas production, mining, photography, and metal plating [1]. CuCN has gained particularly wide recognition owing to its unique characteristics, including luminescence, bioactivity, long-range magnetic order, and electron transfer properties [2]. Moreover, CuCN is also valuable in the crystal engineering field. The CN group acts as a conservative connector to produce a linear $-\text{Cu}-\text{CN}-$ chain in CuCN. Cu^+ ions favor tetrahedral or trigonal coordination in the presence of pyridyl and cyanide groups. This offers the possibility of expanding the arrangement of framework structures due to the strong coordinating properties of the ligands as well as their ability to act as connectors between various metal centers [3]. The structural properties of CuCN and AgCN are relatively similar. Both compounds exist in the form of more than one polymorph. Unlike other cyanides, they are presumed to form $-\text{Cu}-\text{CN}-\text{Cu}-\text{CN}-$ chains [4, 5]. The basic structure of CuCN exhibits static and large thermal displacement of the chain composed of CN or NC groups, which makes the structure formation problematic [6]. Despite the existence of numerous conventional synthetic routes for the preparation of metal cyanides, they mostly utilize toxic anions (e.g., cyanide), which can result in serious health issues affecting the nervous, vascular, cardiac, visual, metabolic, and endocrine systems [7].

Recently, an environmentally friendly approach called pulsed laser ablation in liquid (PLAL) has been proposed as an attractive alternative to the typical chemical methods. The advantages of this surfactant-free technique include the lack of toxicity, speed, and absence of byproducts; therefore, it can be applied for the production of various nano- to submicron-sized materials [8]. Moreover, PLAL is highly energy

efficient and can be employed for the preparation of inorganic/organic colloids without the necessity for chemical reducing agents. PLAL enables the regulation of various properties of materials, e.g., their shape, size, crystalline phase, and chemical composition, by controlling the working parameters, such as the laser wavelength and power, time as well as reaction solvent [9–12]. Focusing the intense pulsed laser on the surface of the desired target immersed in a liquid medium results in the creation of cavitation bubbles, which rapidly expand and collapse within a few microseconds to enable the nucleation and formation of the expected materials [13]. In this work, we employed PLAL in acetonitrile as a facile one-pot technique for the synthesis of CuCN. Considering potential applications, particles, which are stable in organic solvents, are desired because they can be used for the fabrication of novel valuable coordination polymers and other hydrophobic materials.

The present study investigated the conditions of PLAL of Cu in various organic nitrile solvents. The process resulted in the selective and efficient formation of CuCN and graphitic carbon (GC)-encapsulated Cu nanoparticles (NPs). During PLAL in various nitrile solvents, such as acetonitrile, propionitrile, and butyronitrile, the optimum laser wavelength was adjusted to 355, 532, and 1064 nm, respectively. The conducted theoretical studies provided insights into the solvent structures, binding energy, and bond dissociation energy during the reaction. The mechanistic studies based on the obtained results revealed that the laser prompted the fragmentation of acetonitrile into CH_3^+ and CN^- . The latter bound to Cu ions, generating CuCN. Intriguingly, the production of cubic-structured CuCN was favored only in acetonitrile, while other highly ordered propionitrile and butyronitrile solvents generated spherically-shaped Cu@GC NPs. The synthesized CuCN and Cu@GC were characterized by various analytical techniques, including X-ray diffraction (XRD), Fourier transform (FT) Raman spectroscopy, field emission scanning electron microscopy (FE-SEM), and energy-dispersive X-ray spectroscopy (EDS). The evaluation confirmed the rapid synthesis of CuCN with a unique surface structure. The outcomes reported herein could be used for the production of new coordination/polymer materials for applications in the fields of catalysis, sensing, and electronics.

2. Experimental Section

2.1 Materials

The Cu plate ($\geq 99.99\%$) was purchased from Sigma-Aldrich, USA. Acetonitrile (high-performance liquid chromatography [HPLC] grade, 99.8%) was obtained from Daejung Chemicals & Metals Co., Ltd, South Korea. Propionitrile ($> 99.0\%$) and butyronitrile ($> 99.0\%$) were acquired from TCI, Japan. All materials were used as received.

2.2 Synthesis of CuCN by PLAL

The detailed experimental setup is illustrated as a schematic diagram in Fig. 1. A Cu plate was immersed in a vial containing 10 mL of a nitrile solvent (acetonitrile, propionitrile, or butyronitrile). Subsequently, the PLAL process was performed using a Q-switched Nd: YAG nanosecond laser exhibiting different

wavelengths (355, 532, and 1064 nm) at a fixed pulse energy of 80 mJ (Continuum Surelite, SLII-10) for 10 min. To focus the laser beam on the surface of the Cu plate, a focusing lens of $f = 30$ mm was used. The final CuCN product was collected by centrifugation of the obtained colloidal solutions and dried at ambient temperature.

2.3 Material characterization

To evaluate the crystallinity of the prepared materials, XRD analysis was conducted (Bruker, D8 Advance A25) using Cu K α radiation ($\lambda = 1.54$ Å) in the $2\theta^\circ$ range of 20 – 60° . The surface morphology, shape, and chemical composition of the synthesized materials were studied by SEM (TESCAN, CLARA) and EDS. Raman spectra were recorded employing a micro-Raman spectrometer with a 632.8 nm He-Ne laser beam as the excitation source (LabRAM HR800, HORIBA, Jobin-Yvon). Quantum chemical calculations were performed using the Gaussian 16 program [14]. Geometry optimization and relative energy calculations for solvents (acetonitrile, propionitrile, and butyronitrile) were conducted by employing a 6-311++G(d,p) [15] basis set using the following two methods: B3LYP [16] and MP2 (second-order Moller–Plesset perturbation theory) [17]. The binding energies of the solvents (acetonitrile, propionitrile, and butyronitrile) were corrected for the basis set superposition error (BSSE) [18–20] using the counterpoise method. The obtained results were further corrected with zero-point vibrational energy.

3. Results And Discussion

3.1 XRD analysis

The formation of materials and their crystallinity were studied by XRD. The XRD patterns of the samples prepared by PLAL of a Cu plate at 355, 532, and 1064 nm in different nitrile solvents are illustrated in Fig. 2 (a–c). Ablation of the Cu plate at 355, 532, and 1064 nm in propionitrile and butyronitrile led to the formation of Cu NPs. The peaks at 43.2° and 50.4° were consistent with face-centered cubic copper NPs (JCPDS #01-085-1326) [21]. These peaks coincided with the diffraction of the (111) and (200) planes, respectively. The patterns of the Cu plate ablated at all wavelengths in acetonitrile revealed additional strong peaks at 25.1° and 29.5° , which were ascribed to the rhombohedral crystal phase of CuCN (JCPDS #96-110-1019). These peaks were indexed to the (101) and (110) crystallographic planes [22]. In addition to CuCN, a trace amount of pure metallic Cu NPs was present in the sample synthesized in acetonitrile, which was confirmed by weak diffraction peaks. However, the amount of CuNPs in this sample was negligible compared to those in the propionitrile and butyronitrile samples.

3.2 FT-Raman analysis

To further identify the molecules and intermolecular bonds, the samples prepared by PLAL of a Cu plate in various nitrile solvents were analyzed by FT-Raman spectroscopy. The FT-Raman spectra of all samples obtained at different laser wavelength (355, 532, and 1064 nm) are shown in Fig. 3 (a–c). As it can be seen, all spectra exhibited D- and G-bands, which are characteristic of GC. Thus, the D-band originated from a second-order process and described disordered carbon. Moreover, the G-band confirmed

the presence of GC layers formed as a result of the Raman scattering process in graphene [23]. The existence of D- and G-bands indicated the formation of pure metallic Cu NPs covered with GC layers during PLAL in nitrile solvents. More pronounced peaks were detected for the samples synthesized in propionitrile and butyronitrile, suggesting the generation of a high amount of Cu NPs. Notably, the spectra of the samples ablated in acetonitrile at 355, 532, and 1064 nm displayed an additional distinctive peak at 2175 cm^{-1} [24]. This peak was attributed to the copper(I) cyanide species, and the observed FT-Raman results were in good agreement with the XRD analysis.

3.3 SEM analysis

The surface morphology and shape of the synthesized materials were studied by SEM. The SEM images of the CuCN sample synthesized in acetonitrile at different laser wavelengths are shown in Fig. 4(a–c). The morphology of all samples formed in acetonitrile exhibited micro-sized cubes. The elements, from which the materials were composed, were further investigated by EDS. It was determined that the obtained microstructures consisted of Cu, C, and N (Fig. 4c (i–iii)). These results further supported the formation of CuCN in acetonitrile regardless of the laser wavelength. In addition, some spherical NPs were found among cubic CuCN (Fig. 4). The NPs were responsible for the characteristic signals of metallic Cu. Figure 4(d) illustrates the SEM image of spherical copper NPs obtained by PLAL of a Cu plate in acetonitrile at a wavelength of 355 nm. The EDS elemental mapping images of the sample revealed the presence of Cu and C atoms (Fig. 4d (i–ii)), which confirmed that the spherical Cu NPs were covered with carbon shells due to availability of alkyl carbons in the solvent. The existence of Cu@GC NPs was also confirmed by XRD and FT-Raman analyses.

Furthermore, the SEM images of samples prepared in propionitrile and butyronitrile are shown in Fig. 5. In contrast to the surface morphology of the material obtained in acetonitrile, in the case of the samples prepared in propionitrile and butyronitrile, the majority of the particles were spherical and no cubical structures were observed. It was found that the final shape of the particles in propionitrile or butyronitrile was not affected by the laser wavelength. The EDS analysis (Fig. 5c (i–ii) and 5f (i–ii)) confirmed that similarly to the spherical particles found in acetonitrile, the spherical NPs in the samples prepared in propionitrile or butyronitrile were composed of Cu and C. Notably, the amount of Cu@GC NPs in propionitrile was significantly higher than in butyronitrile [25].

3.4 Theoretical calculations

Table 1
Binding energies (C–C bond) calculated for the studied organic nitriles
(kJ/mol)

Method	Acetonitrile	Propionitrile		Butyronitrile		
	BE ^a	BE ^a	BE ^b	BE ^a	BE ^b	BE ^c
B3LYP	530.78	516.14	342.55	518.87	381.16	329.45
MP2	611.63	609.42	421.37	612.89	415.04	421.12
CCD	607.63	602.88	378.64	605.71	389.39	375.7
CCSD	510.53	505.1	358.08	507.73	388.31	354.49
CAM-B3	544.46	534.92	356.41	538.49	391.88	345.23
M062X	552.47	542.47	379.86	545.23	410.43	372.75
LC-wPBE	553.16	581.59	365.2	544.86	394.39	355.29
LC-BLYP	576.29	566.59	380.16	571.38	411.78	371.35
M052X	564.94	554.55	376.66	557.84	410.94	368.99
*BE ^a : C ₁ –C ₂ Binding energy ^a *BE ^b : C ₂ –C ₃ (C ₃ –C ₄) Binding energy ^b *BE ^c : C ₃ –C ₂ Binding energy ^c *Basis set: 6-311 ++ G(d,p)						

Experimental analysis confirmed the formation of CuCN only in acetonitrile, which was supported by the conducted theoretical studies. Overall, analysis of all of the experimental results was in full agreement with the theoretical calculations.

The phenomenon of fragmentation of solvent molecules during PLAL caused by the difference in the bond energy between atoms could be considered as the solvent effect [26]. Based on the theoretical calculations summarized in Table 1, it was evident that the formation of CuCN was only favorable in acetonitrile, which was attributed to the good availability of the cyano groups immediately after fragmentation of the solvent molecules. The dissociation of the bond between C₁ and C₂ resulted in the formation of the methyl cation (CH₃⁺) and cyanide anion (CN[−]) (Fig. 6). Similarly to Ag(I), the Cu NPs generated during PLAL displayed strong binding affinity. The electron configuration of Cu is [Ar]3d¹⁰4s¹. The filled d-subshell promotes the formation of stable complexes with ligands by π -back bonding [22]. The back donation of the ligand to the metal through sigma (σ) bonding and further transfer of the

electron density back into the π orbitals of the ligand have also reported [27]. The CN^- species has an overall negative charge due to the presence of a lone pair of electrons on either side of the atom. Consequently, strong complexation between CN^- and Cu^+ occurs. Moreover, the majority of Cu ions produced during PLAL bind to the cyano groups due to the strong affinity of these moieties toward each other. This is caused by $d_{\pi}-p_{\pi^*}$ back donation of the d^{10} Cu(I) orbitals to the low-lying π^* orbitals of CN^- [28]. In addition to the formation of CuCN in acetonitrile, a few spherical Cu NPs covered with GC shells were observed due to the presence of a methyl group in the solvent. Nonetheless, the carbon source was insufficient to produce many spherical Cu@GC NPs in acetonitrile.

Another interesting observation was made when propionitrile and butyronitrile were used as solvents for PLAL of a Cu plate. Structural analysis revealed the formation of spherical NPs composed of Cu and C. The characteristic peaks of Cu as well as D- and G-bands of GC were detected in the XRD patterns and FT-Raman spectra of these samples, respectively. Moreover, the characteristic peaks corresponding to CuCN were not detected in the following spectra, and no traces attributed to cubic particles were observed during the FE-SEM analysis. To explain these outcomes, we conducted theoretical calculations of the binding energies (Table 1). Bonds between carbon atoms C_1-C_2 and C_2-C_3 were considered (Fig. 6). Both C_1-C_2 and C_2-C_3 exhibit distinct binding energy (BE^a and BE^b , respectively). The values of BE^b , i.e., the energy between the C_2 and C_3 atoms in propionitrile, and BE^c in butyronitrile were lower. These bonds underwent dissociation during PLAL, releasing a large amount of alkyl carbons, which further deposited on the surface of Cu NPs to form GC layers. Once Cu NPs were encapsulated in carbon shells, further interactions with the cyano groups were not possible. The GC layers hindered the growth of Cu NPs and prevented external impact, enhancing the stability of the material. Thus, the shapes of all particles synthesized in propionitrile and butyronitrile were spherical. Accordingly, the formation of CuCN upon the elongation of the carbon chain in organic nitriles was less likely. It was also confirmed that the binding energies of C–C and $\text{C}\equiv\text{N}$ in acetonitrile were 530.78 and 1167.64 kJ/mol. Hence, it was determined that the $\text{C}\equiv\text{N}$ bond was stronger than the C–C bond (Fig. 7, Table 2). Consequently, it was predicted that CuCN was formed by the cleavage of the C–C bond during PLAL.

Table 2
Binding energies (C \equiv N bond) calculated for various organic nitrile solvents (kJ/mol)

	C \equiv N binding energy (kJ/mol)		
	Acetonitrile	Propionitrile	Butyronitrile
B3LYP	1167.64	1166.88	1167.51
MP2	1249.62	1250.38	1250.82
CCD	1117.79	1117.78	1118.03
CAM-B3	1172.4	1175.78	1176.43
M062X	1192.31	1191.99	1192.36
*C \equiv N binding energy (kJ/mol)			
*Basis set: 6-311 + + G(d,p)			

4. Conclusions

In summary, a facile one-pot synthesis of CuCN was performed using PLAL in acetonitrile. Theoretical studies on the formation of CuCN were conducted using quantum chemical calculations by performing basic sets of B3LYP and MP2. It was found that the formation CuCN was favorable only in acetonitrile, which was attributed to the high availability of the CN⁻ moiety immediately following the fragmentation of acetonitrile under PLAL. In contrast, the use of highly ordered nitrile solvents, such as propionitrile and butyronitrile, resulted in a release of a high amount of alkyl carbons, which further deposited on the surface of Cu NPs to form GC layers (Cu@GC). The formation of cubic CuCN and spherical Cu@GC structures was examined by XRD, FT-Raman, FE-SEM, and EDS. The results of the present study involving PLAL-assisted synthesis of CuCN with a unique surface structure can be utilized for the development of novel metal–polymer materials for applications in various fields.

Declarations

Data availability:

The data which support for this research findings are available and can provided based on the request to the corresponding authors.

Acknowledgments:

This research was supported by Korea Basic Science Institute (National research Facilities and Equipment Center) grant funded by the Ministry of Education (No. 2019R1A6C1010042). Prof. M. Y. Choi and Dr. J. Theerthagiri acknowledge the financial support from National Research Foundation of Korea (NRF), (2019R1A2C1009871, 2019H1D3A1A01071209). Dr. S. J. Lee acknowledge the financial support from National Research Foundation of Korea (NRF-2020R1I1A1A01065748). SEM, EDS, and micro-Raman instruments are used in the Core-Facility Center for Photochemistry & Nanomaterials.

Author contributions:

Talshyn Begildayeva - conceptualization, investigation, writing, and data curation; Ahreum Ahn - investigation, writing, and data curation; Shreyanka Shankar Naik - formal analysis and data curation; Seung Jun Lee - investigation, and data curation; Jayaraman Theerthagiri - writing-review and editing; Tae Ho Kim – conceptualization and data curation; Myong Yong Choi - funding acquisition, project administration, and supervision.

Competing interests:

No conflict of interest.

References

1. Saadatmand, M., S. Sadeghpour, and J. Mohandesi, *Optimisation of brass plating condition in plating of patented steel wire*. Surface Engineering, 2011. **27**: p. 19-25.
2. Deng, H., et al., *Synthesis of New Copper Cyanide complexes via the Transformation of Organonitrile to Inorganic Cyanide*. Inorganic Chemistry, 2008. **47**(13): p. 5866-5872.
3. Liang, S.-W., et al., *Hydrothermal synthesis and crystal structure of a novel cyanide-bridged double helical copper(I) coordination polymer $[\text{Cu}_3(\text{CN})_3(\text{phen})]_n$* . Inorganic Chemistry Communications, 2006. **9**(12): p. 1312-1314.
4. Gupta, M., et al., *Lattice Dynamics and Thermal Expansion Behavior in Metal Cyanides, MCN (M=Cu, Ag, Au): Neutron Inelastic Scattering and First Principles Calculations*. Physical Review B, 2015. **93**.
5. Hibble, S. and A. Chippindale, *The threading of $[(\text{CuCN})_2(\mu\text{-}4,4'\text{-bpy})]$ sheets by CuCN chains*. Zeitschrift für anorganische und allgemeine Chemie, 2005. **631**: p. 542-545.
6. Hibble, S., et al., *Copper(I) Cyanide: A Simple Compound with a Complicated Structure and Surprising Room-Temperature Reactivity*. Angewandte Chemie (International ed. in English), 2004. **43**: p. 628-30.

7. Simeonova, F.P., L. Fishbein, and W.H. Organization, *Hydrogen cyanide and cyanides: human health aspects*. 2004: World Health Organization.
8. Lee, S.H., et al., *Selective synthesis of Au and graphitic carbon-encapsulated Au (Au@GC) nanoparticles by pulsed laser ablation in solvents: Catalytic Au and acid-resistant Au@GC nanoparticles*. Applied Surface Science, 2020. **506**: p. 145006.
9. Lee, S.J., et al., *Efficient recovery of palladium nanoparticles from industrial wastewater and their catalytic activity toward reduction of 4-nitrophenol*. Chemosphere, 2021. **262**: p. 128358.
10. Lee, S.J., et al., *Plasmonic ZnO/Au/g-C₃N₄ nanocomposites as solar light active photocatalysts for degradation of organic contaminants in wastewater*. Chemosphere, 2021. **263**: p. 128262.
11. Begildayeva, T., et al., *Production of copper nanoparticles exhibiting various morphologies via pulsed laser ablation in different solvents and their catalytic activity for reduction of toxic nitroaromatic compounds*. Journal of Hazardous Materials, 2020: p. 124412.
12. Lee, S.J., et al., *Eco-friendly synthesis of lignin mediated silver nanoparticles as a selective sensor and their catalytic removal of aromatic toxic nitro compounds*. Environmental Pollution, 2020: p. 116174.
13. Jung, H.J. and M.Y. Choi, *One-pot synthesis of graphitic and nitrogen-doped graphitic layers on nickel nanoparticles produced by pulsed laser ablation in liquid: Solvent as the carbon and nitrogen source*. Applied Surface Science, 2018. **457**: p. 1050-1056.
14. Frisch, M.J., et al., *Gaussian 16 Rev. B.01*. 2016: Wallingford, CT.
15. Ditchfield, R., W.J. Hehre, and J.A. Pople, *Self-Consistent Molecular-Orbital Methods. IX. An Extended Gaussian-Type Basis for Molecular-Orbital Studies of Organic Molecules*. The Journal of Chemical Physics, 1971. **54**(2): p. 724-728.
16. Becke, A.D., *Density-functional thermochemistry. III. The role of exact exchange*. The Journal of Chemical Physics, 1993. **98**(7): p. 5648-5652.
17. Head-Gordon, M., J.A. Pople, and M.J. Frisch, *MP2 energy evaluation by direct methods*. Chemical Physics Letters, 1988. **153**(6): p. 503-506.
18. Balabin, R.M., *Enthalpy difference between conformations of normal alkanes: Intramolecular basis set superposition error (BSSE) in the case of n-butane and n-hexane*. The Journal of Chemical Physics, 2008. **129**(16): p. 164101.
19. Dunning, T.H., *A Road Map for the Calculation of Molecular Binding Energies*. The Journal of Physical Chemistry A, 2000. **104**(40): p. 9062-9080.

20. Liu, B. and A.D. McLean, *Accurate calculation of the attractive interaction of two ground state helium atoms*. The Journal of Chemical Physics, 1973. **59**(8): p. 4557-4558.
21. Leung, A.H.M., et al., *Cu/M:ZnO (M = Mg, Al, Cu) colloidal nanocatalysts for the solution hydrogenation of carbon dioxide to methanol*. Journal of Materials Chemistry A, 2020. **8**(22): p. 11282-11291.
22. Wang, J., M.F. Collins, and G.P. Johari, *CuCN: An orientational glass*. Physical Review B, 2002. **65**(18): p. 180103.
23. Kaniyoor, A. and R. Sundara, *A Raman spectroscopic investigation of graphite oxide derived graphene*. AIP Advances, 2012. **2**: p. 032183-032183.
24. Lukey, G.C., et al., *Raman study on the speciation of copper cyanide complexes in highly saline solutions*. Hydrometallurgy, 1999. **53**(3): p. 233-244.
25. Hao, C., F. Xiao, and Z. Cui, *Preparation and structure of carbon encapsulated copper nanoparticles*. Journal of Nanoparticle Research, 2008. **10**(1): p. 47-51.
26. Bordwell, F.G. and W.-Z. Liu, *Solvent Effects on Homolytic Bond Dissociation Energies of Hydroxylic Acids*. Journal of the American Chemical Society, 1996. **118**(44): p. 10819-10823.
27. Nelin, C.J., P. Bagus, and M. Philpott. *The nature of the bonding of CN to metals and organic molecules*. 1987.
28. Romao, C., et al., *A high-pressure micro-Raman spectroscopic study of copper cyanide, CuCN*. Journal of Materials Science, 2010. **45**: p. 2518-2520.

Figures

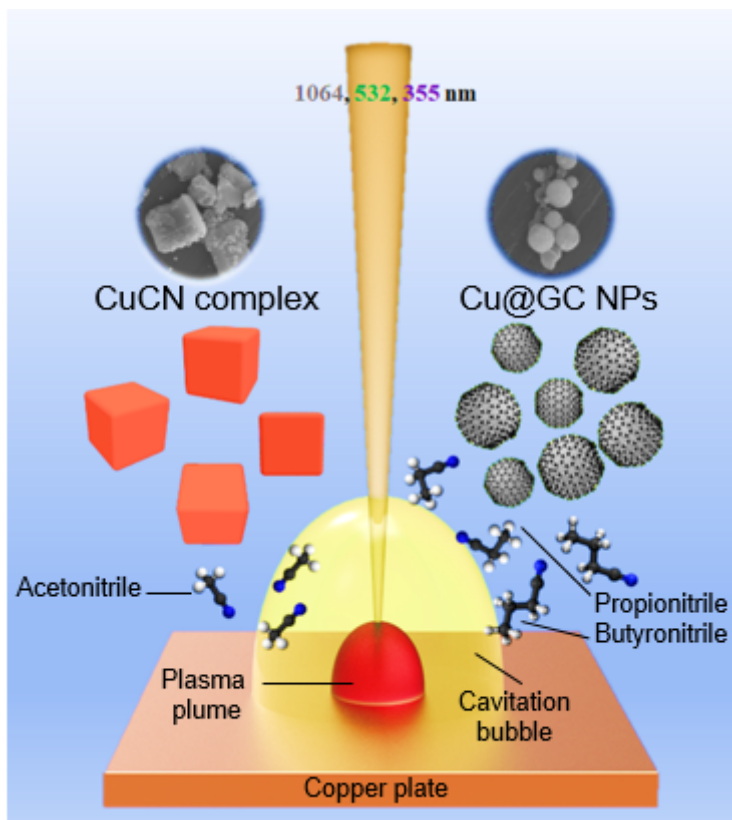


Figure 1

PLAL (1064, 532, and 355 nm) of a Cu target in various nitrile solvents (acetonitrile, propionitrile, or butyronitrile) leading to the formation of cubic CuCN and spherical Cu@GC.

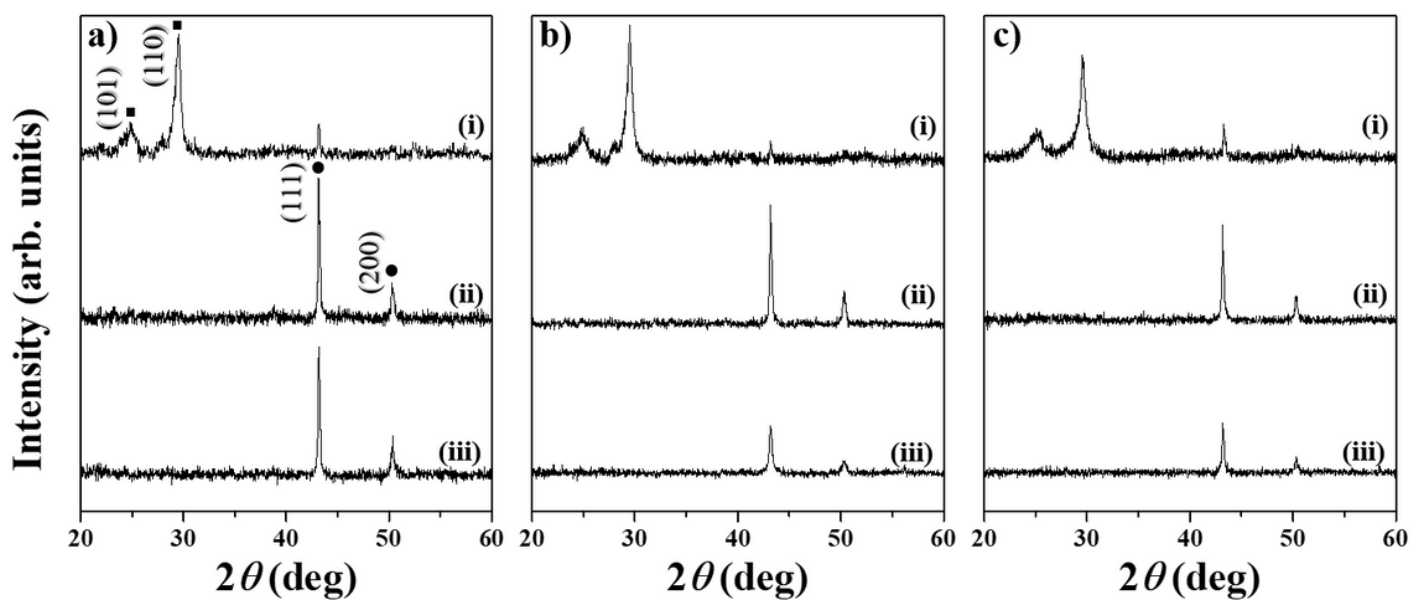


Figure 2

XRD patterns of samples synthesized by PLAL of a Cu plate in (i) acetonitrile, (ii) propionitrile, and (iii) butyronitrile at different laser wavelengths of (a) 355, (b) 532, and (c) 1064 nm. Characteristic peaks of

metallic Cu at 43.2° and 50.4° denoted as (•) were consistent with JCPDS #01-085-1326. The CuCN peaks at 24.9° and 29.5° (JCPDS #96-110-1019) are indicated by (■).

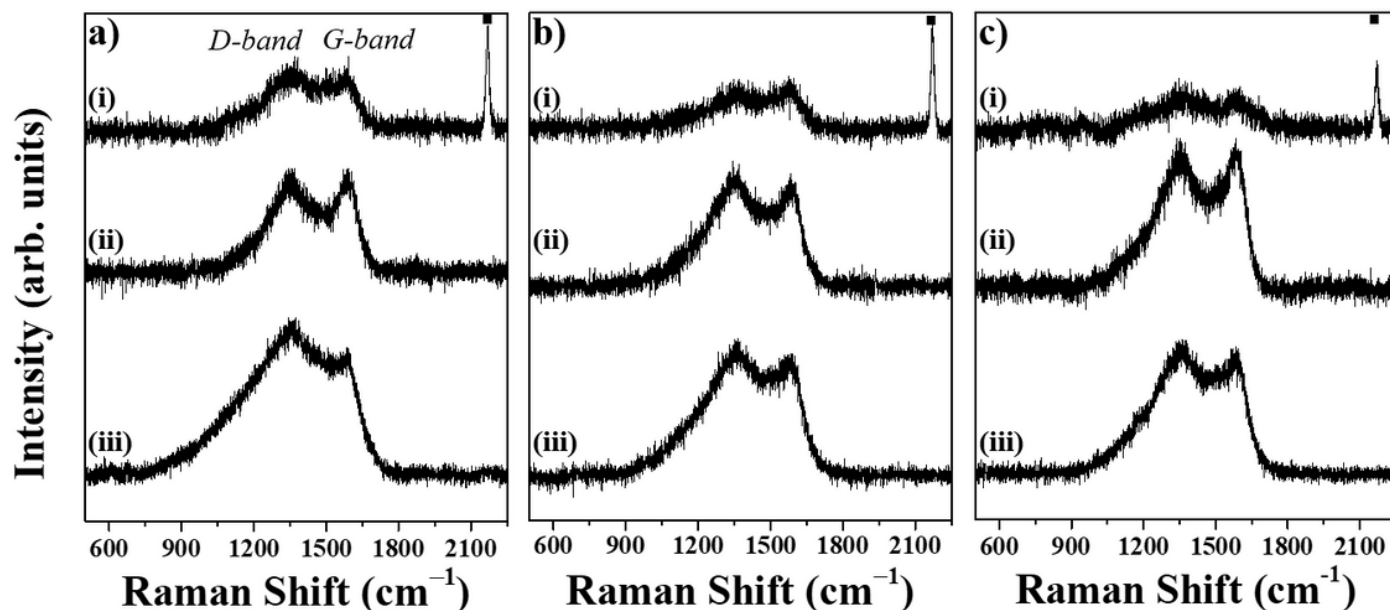


Figure 3

FT-Raman spectra of samples synthesized by PLAL of a Cu plate in (i) acetonitrile, (ii) propionitrile, and (iii) butyronitrile at different laser wavelengths of (a) 355, (b) 532, and (c) 1064 nm. Peaks at 1350 and 1590 cm^{-1} correspond to the D- and G-bands of the sp^2 hybridized carbon, respectively. They were attributed to GC shells on the surface of spherical Cu NPs. The characteristic CuCN peak at 2170 cm^{-1} is indicated by (■).

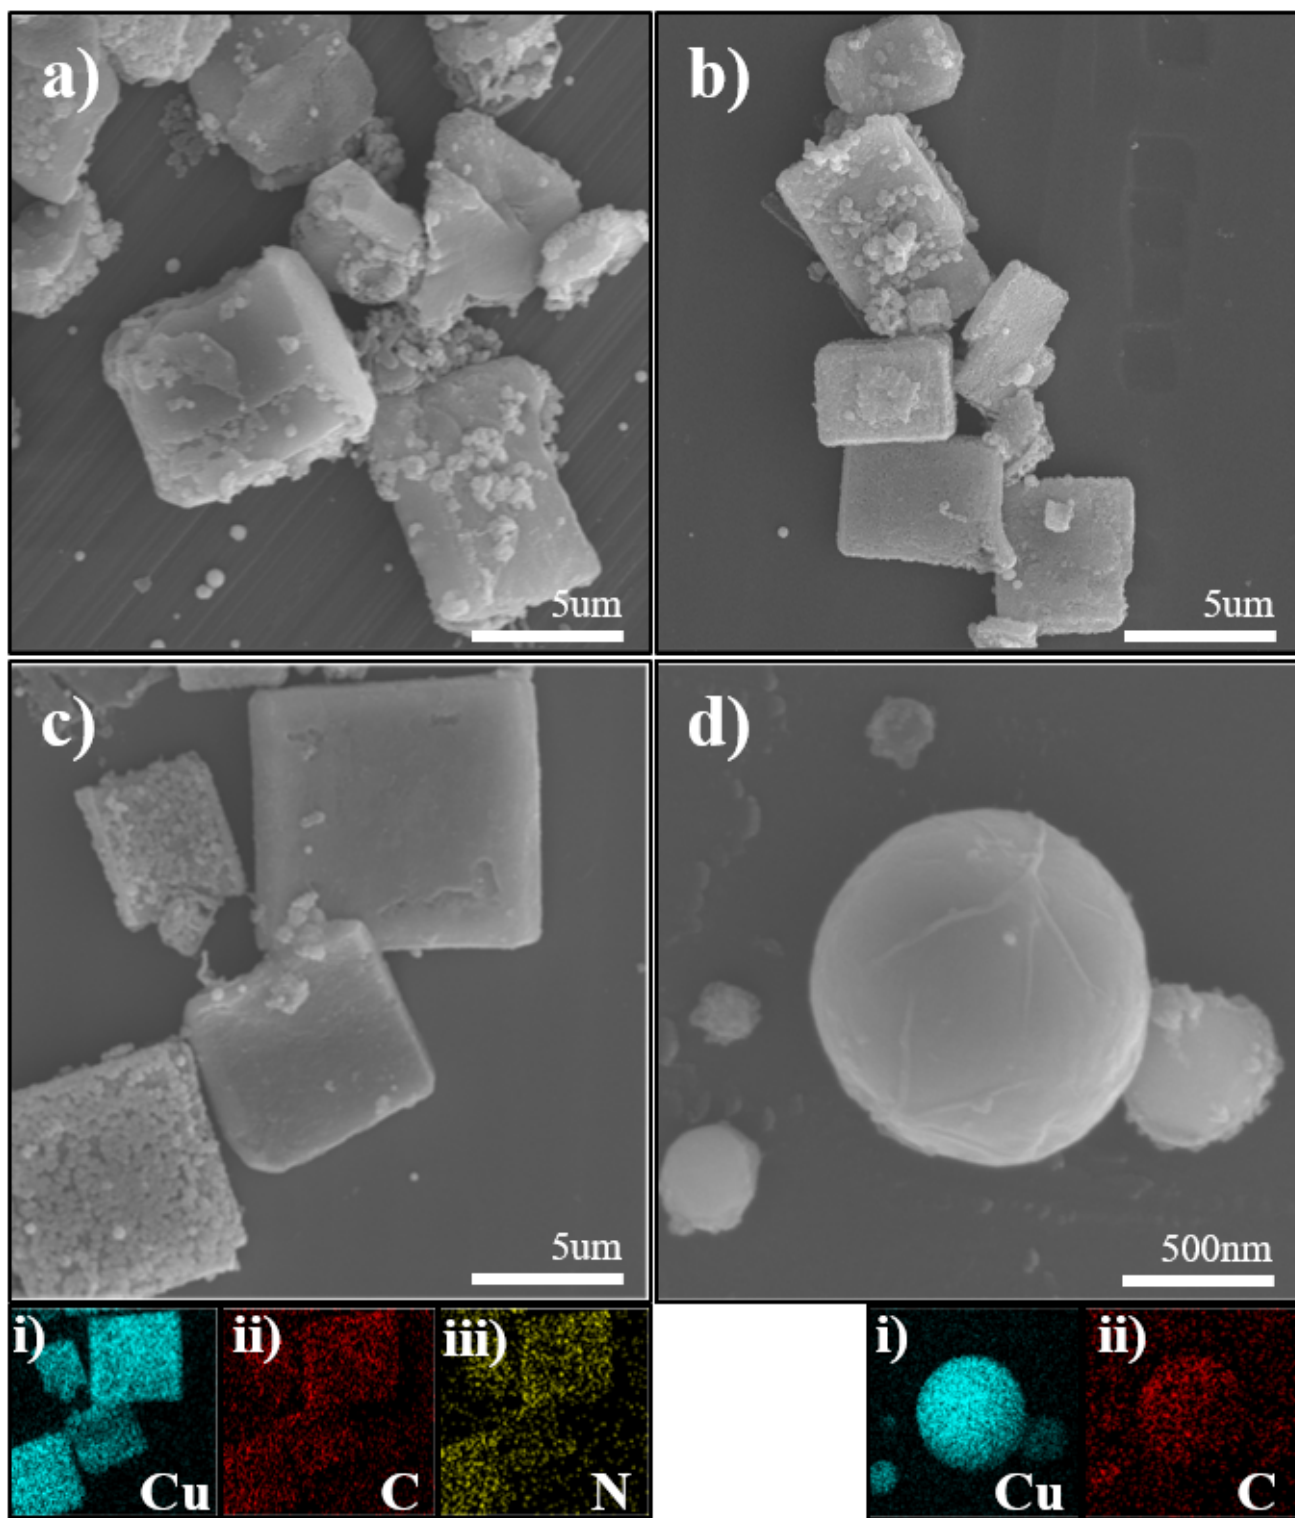


Figure 4

SEM images of samples prepared by PLA of a Cu plate in acetonitrile at (a) 355, (b) 532, (c) and 1064 nm as well as of (d) spherical Cu NPs covered with carbon shells present in all of the above samples. EDS analysis of (c, i–iii) cubic species and (d, i–ii) spherical NPs.

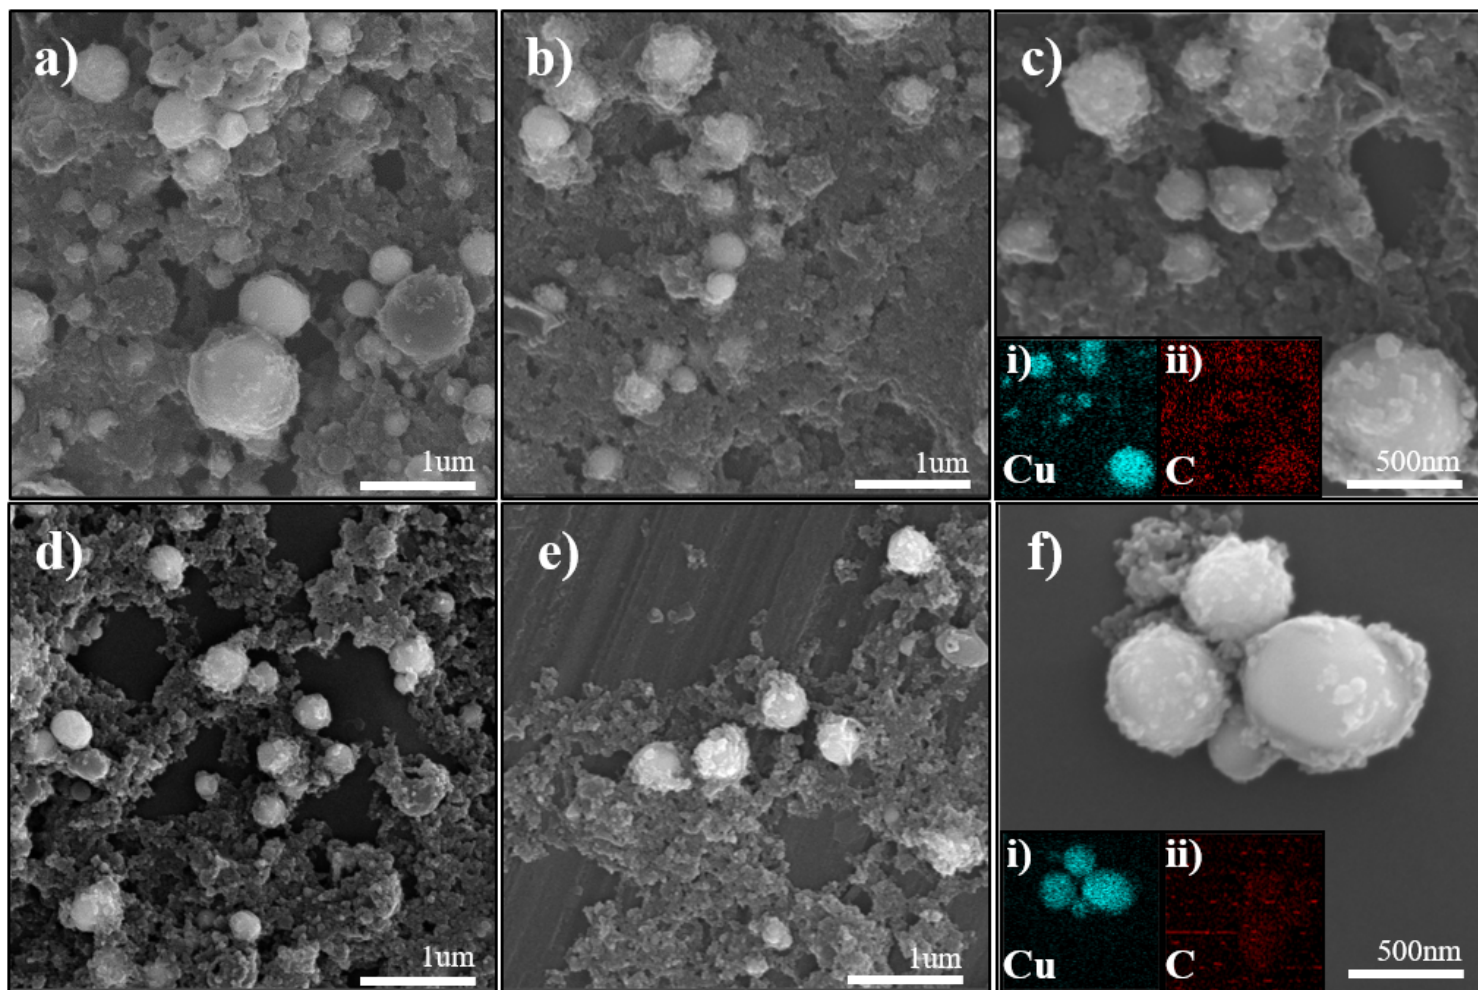


Figure 5

SEM images of samples synthesized in propionitrile at (a) 355, (b) 532, and (c) 1064 nm. (c, i–ii) EDS analysis of the corresponding sample. SEM images of the material prepared in butyronitrile at (d) 355, (e), 532, and (f) 1064 nm. (f, i–ii) EDS analysis of the particles prepared in butyronitrile.


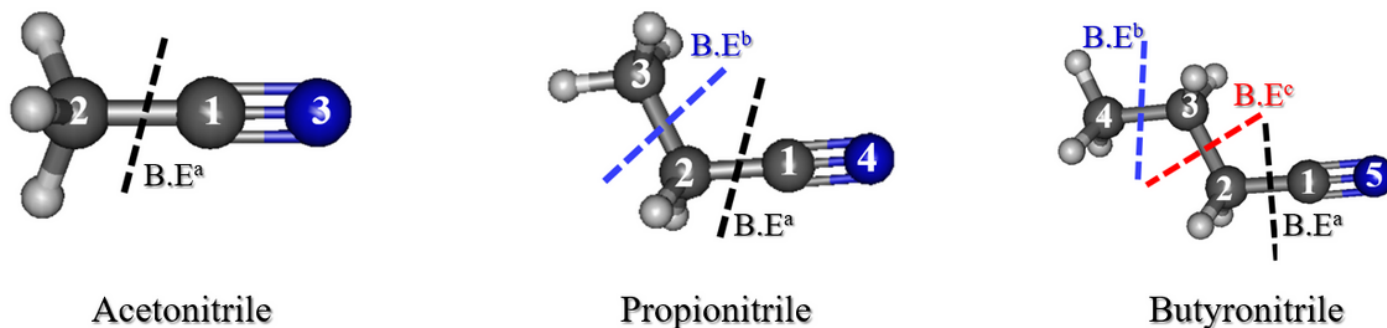



Figure 6

Structures of organic nitrile solvents showing the separated bonds, for which the binding energy (BE) was calculated. BE^a – bond between the C1 and C2 atoms (C1–C2 in all nitriles), BE^b – bond between two


carbon atoms (C2–C3 in propionitrile or C3–C4 in butyronitrile), BEc – bond between the C3 and C2 carbon atoms (C3–C2) in butyronitrile.

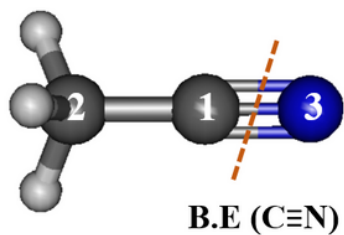

Acetonitrile

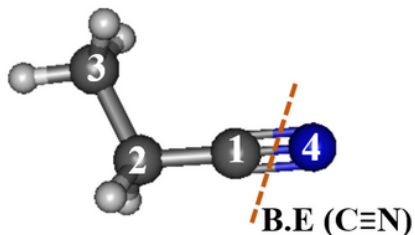

Propionitrile

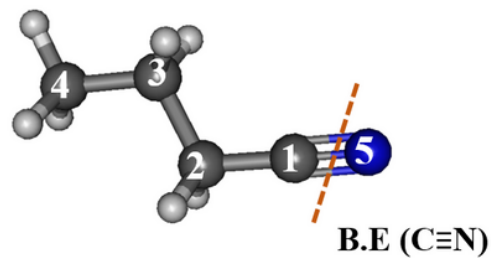

Butyronitrile

Figure 7

Structure of organic nitrile solvents showing the separated $\text{C}\equiv\text{N}$ bonds, for which the binding energy was calculated.