

Supplementary Information:

Non-Amontons Frictional Behaviors of Grain Boundaries at Layered Material Interfaces

Yiming Song,^{†,1} Xiang Gao,^{†,2} Rémy Pawlak,¹ Shuyu Huang,^{1,3} Antoine Hinaut,¹ Thilo Glatzel,¹
Oded Hod,^{*,2} Michael Urbakh,^{*,2} Ernst Meyer^{*,1}

¹ Department of Physics, University of Basel, Basel 4056, Switzerland.

² Department of Physical Chemistry, School of Chemistry, The Raymond and Beverly Sackler Faculty of Exact Sciences and The Sackler Center for Computational Molecular and Materials Science, Tel Aviv University, Tel Aviv 6997801, Israel.

³ Key Laboratory for Design and Manufacture of Micro-Nano Biomedical Instruments, School of Mechanical Engineering, Southeast University, Nanjing 211189, China.

*Corresponding authors: Email: urbakh@tauex.tau.ac.il, odedhod@tauex.tau.ac.il, and ernst.meyer@unibas.ch

In this supplemental material, we provide additional details regarding the following aspects of the study reported in the main text:

1. Sample Preparation
2. Tip Preparation and Characterization
3. Determination of Grain Boundary Angle
4. Characterization of Additional Grain Boundaries
5. Energy Dissipation Route and Average Friction Calculation
6. Reproducibility and Additional Grain Boundary Friction Measurements
7. Molecular Dynamics Simulations

1. Sample Preparation

The Pt(111) surface was cleaned by cycles of Ar⁺ ion sputtering (energy of 1.2-1.8 keV under a preparation chamber pressure of 3×10^{-6} mbar for 10 min) and high temperature annealing using a home-made radio frequency heater. The surface was exposed to oxygen atmosphere (under a preparation chamber pressure of 5×10^{-8} mbar for 15 min) prior to the first annealing cycle to remove the carbide impurities. During the annealing procedure, the system was heated at a temperature of 1,400 K for a period of 20 min. Following this surface preparation step, monolayer polycrystalline graphene (PolyGr) was grown by means of high-temperature flash in ultrahigh vacuum (UHV). The sample was heated to a temperature of 1,073 K, and high purity ethylene was dosed onto the hot Pt(111) surface directly using a nozzle for 2 min under a preparation chamber pressure of 2×10^{-8} mbar. After that, the sample was kept at 1,073 K for an extra 20 min, followed by a slow cooling down process to room temperature at a rate of 1 K/sec. Figure S1 presents an example of a non-contact atomic force microscope (NC-AFM) topography map of (a) an atomically clean Pt(111) surface prior to graphene growth, and (b) the same surface (but different location) after the graphene growth process.

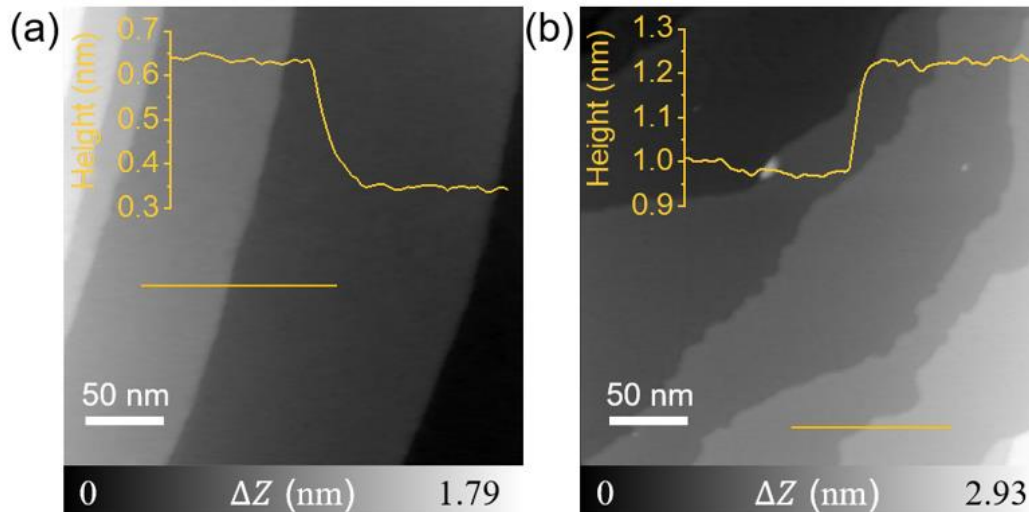


Figure S1. Sample surface characterization. Topographic images of an atomically clean Pt(111) surface (a) prior to and (b) following graphene growth. Insets show the height profiles across a single atomic step edge (orange curves) measured by NC-AFM. Measurement parameters: $A_{1st} = 3$ nm and $\Delta f_{1st} = -14$ Hz in panel (a) and $A_{1st} = 3$ nm and $\Delta f_{1st} = -15$ Hz in panel (b).

2. Tip Preparation and Characterization

The AFM probe (PPP-CONT, Nanosensors) used for the friction measurements was annealed in UHV at a temperature of 473 K for several hours to remove residual contaminants from the tip surface prior to performing the friction force measurements. This was followed by Ar^+ ion sputtering of the tip for 2 min to remove the native silicon dioxide covering the tip. The normal and lateral forces acting on the probe were calibrated according to the procedures described in Ref. 1. Scanning electron microscopy (SEM) was used to determine the dimensions of the cantilever and tip radius (typically less than 7 nm), as shown in Fig. S2.

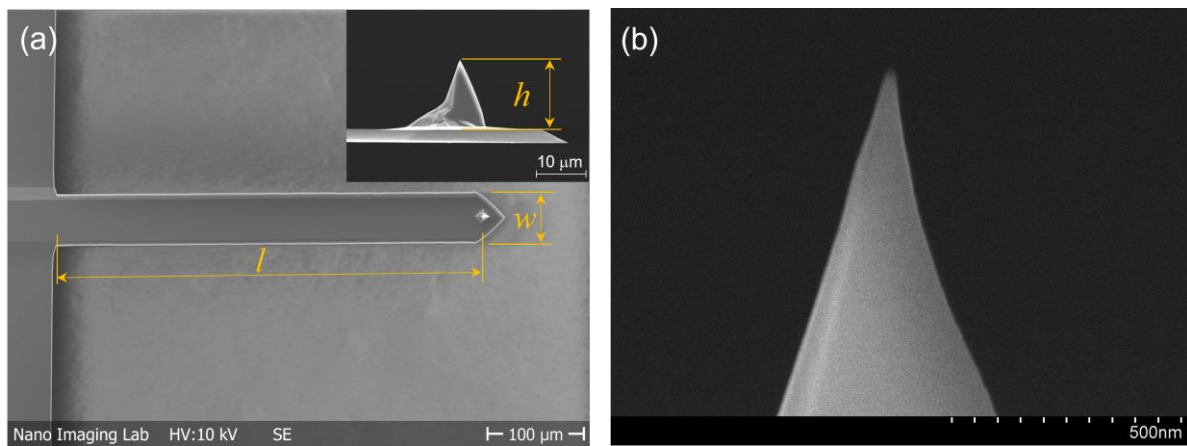


Figure S2. SEM characterization of the AFM probe. (a) Dimensions of the cantilever and the height of the tip. (b) Zoom-in image of the tip.

3. Determination of Grain Boundary Angle

The GB angle θ_{GB} , i.e., the relative orientation configuration between two neighboring grains, is determined by fast Fourier transform (FFT) analysis of the atomic structures of the PolyGr layer provided by high-resolution characterization images (see, e.g., Fig. S3). The GB misfit angle, θ_{GB} , is obtained by measuring the angle between the two rotated FFT patterns (see white arrows in Fig. S3b), yielding, in this case, $\theta_{\text{GB}} = 21.43 \pm 0.66^\circ$. The inner bright area in the FFT image is related to the long-range moiré superstructures.

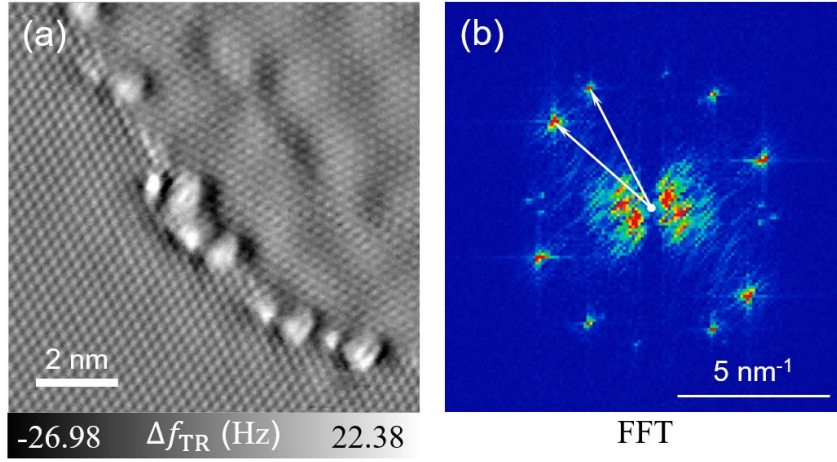


Figure S3. Characterization of the misfit angle of the GB appearing in Fig. 1c of the main text. (a) High-resolution NC-AFM image of the moiré and atomic structure near a GB of a PolyGr surface using the torsional frequency shift Δf_{TR} mode (same as Fig. 1c of the main text). (b) FFT of panel a, giving a GB misfit angle of $\theta_{\text{GB}} = 21.43 \pm 0.66^\circ$.

In addition, GB misfit angles have been determined independently using atomic resolution contact AFM lateral force maps and high-resolution low-temperature ($< 5\text{K}$) scanning tunneling microscope (LT-STM) topography images. Fig. S4a presents such a high-resolution lateral force map for the GB appearing in Fig. 2a of the main text, the misfit angle of which is determined via FFT analysis (Fig. S4b) to be $\theta_{\text{GB}} = 2.35 \pm 0.10^\circ$.

For small angle GBs ($\theta_{\text{GB}} < 10^\circ$) with discrete dislocations, each GB dislocation can form an individual upward protrusion.² This allows us to validate the FFT determination of the GB misfit angle by comparing the extracted θ_{GB} values to those obtained independently from the periodic distance, D , between neighboring GB protrusions, using Frank's equation:^{3,4}

$$\theta_{\text{GB}} = 2 \arcsin \frac{|\vec{b}_{(1,0)}|}{2D}. \quad (\text{S1})$$

Here, $\vec{b}_{(1,0)}$ is the Burgers vector of the most common edge-sharing heptagon-pentagon pair dislocation in graphene ($|\vec{b}_{(1,0)}| = 2.46 \text{ \AA}$, see Fig. S5a). For the GB appearing in Fig. S4a, periodic features (e.g., grey dots on the left of the GB) separated by $D = 5.34 \pm 0.23 \text{ nm}$ are observed. Substituting this value into Eq. S1, we obtain a theoretical estimation of the GB angle of $\theta_{\text{GB}} \approx 2.64^\circ$, in good agreement with our FFT analysis value of $\theta_{\text{GB}} = 2.35 \pm 0.10^\circ$.

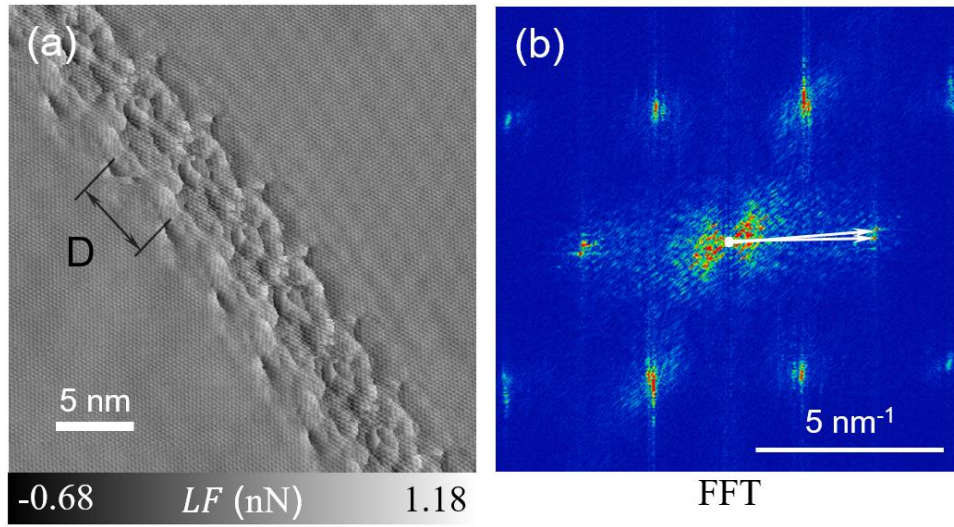


Figure S4. Characterization of the misfit angle of the GB appearing in Fig. 2a of the main text. (a) High-resolution lateral force map of the GB region. The averaged distance between neighboring dislocations is $D = 5.34 \pm 0.23 \text{ nm}$, yielding a misfit angle of $\theta_{\text{GB}} \approx 2.64^\circ$, via Eq. S1. (b) Corresponding FFT analysis of panel a, giving a GB angle of $\theta_{\text{GB}} = 2.35 \pm 0.10^\circ$.

The summarized experimental results of D vs. θ_{GB} (obtained via FFT analysis) as well as the corresponding predictions from Eq. S1 are presented in Fig. S5b. The good agreement between the experimental results and the theoretical predictions from Eq. S1, especially in the low GB misfit angle regime, further validates our experimental determination of the GB misfit angle. Furthermore, it also suggests that the GBs obtained in this study are mainly of (1,0) type (see Fig. S5a) heptagon-pentagon pair dislocation, the Burgers vector of which was used for the determination of the misfit angle via Eq. S1.

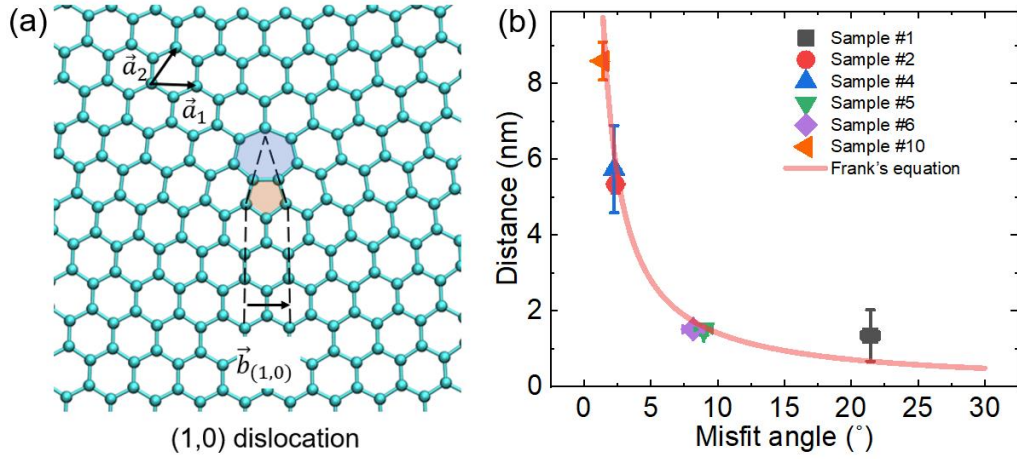


Figure S5. Relation between GB misfit angle and inter-protrusion distance. (a) Illustration of the (1,0) type pentagon-heptagon dislocation and its corresponding Burgers vector. (b) Inter-protrusion distance dependence on the GB misfit angle as obtained using FFT analysis of high-resolution topography maps (symbols) compared to the theoretical prediction of Frank's equation (red line, Eq. S1). Error bars represent the corresponding standard deviation obtained by performing at least 3 to 5 independent measurements.

4. Characterization of Additional Grain Boundaries

In the main text, we presented the analysis of two GBs. Here, we provide LT-STM results for additional GBs of different misfit angles. The experiments were carried out using a commercial low temperature (~ 5 K) qPlus STM/AFM instrument (Omicron GmbH) operated with Nanonis RC5 electronics, which prevents thermal drifts. The polycrystalline graphene samples were transferred from the room-temperature UHV AFM apparatus into the low-temperature STM/AFM system via an UHV transfer suitcase (Ferrovac, base pressure of $\leq 5 \times 10^{-10}$ mbar). Before the STM measurement, a soft annealing process was conducted at a temperature of 400 K for 10 min to remove potential contaminants. All STM images were acquired in the constant-current mode. Based on FFT analysis of the LT-STM topography images, we identified a series of GB angles in the range of 2 – 28° (see Figs. S6-S10).

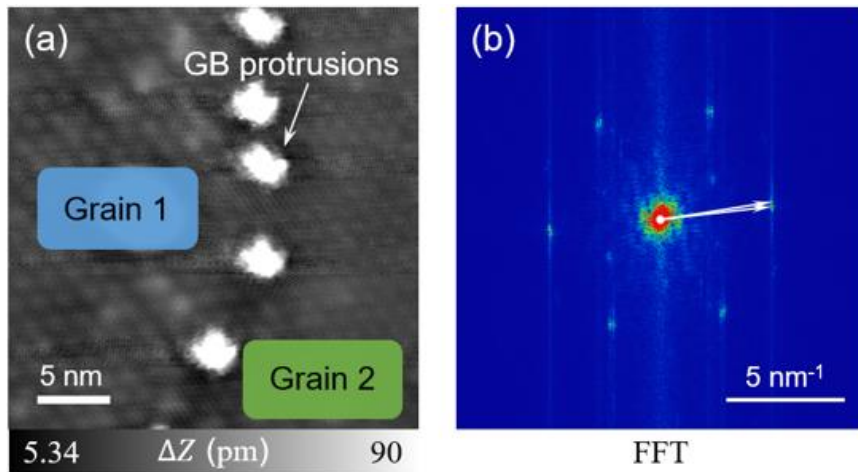


Figure S6. Characterization of a GB with misfit angle of $\theta_{GB} = 2.25 \pm 0.09^\circ$. (a) High resolution LT-STM image showing the moiré and the atomic structure on both sides of a GB. The average distance between neighboring GB protrusions is $D = 5.74 \pm 1.15$ nm. (b) The corresponding FFT map. The white arrows mark the two rotated FFT patterns associated with the atomic lattices of the two grains. Measurement parameters: $V_{tip} = 3$ mV and $I = 1$ pA.

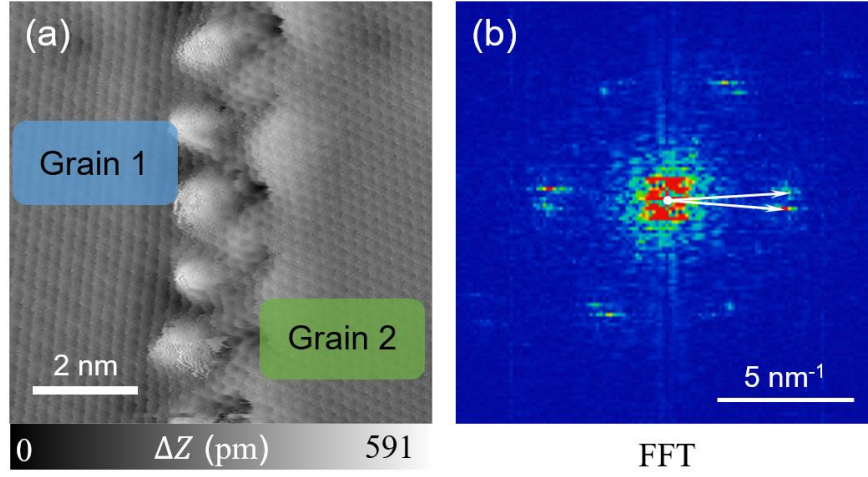


Figure S7. Characterization of a GB with misfit angle of $\theta_{\text{GB}} = 8.15 \pm 0.76^\circ$. (a) High resolution LT-STM image showing the moiré and the atomic structure on both sides of a GB. The average distance between neighboring GB protrusions is $D = 1.52 \pm 0.12$ nm. (b) The corresponding FFT map. The white arrows mark the two rotated FFT patterns associated with the atomic lattices of the two grains. Measurement parameters: $V_{\text{tip}} = 12$ mV and $I = 50$ pA.

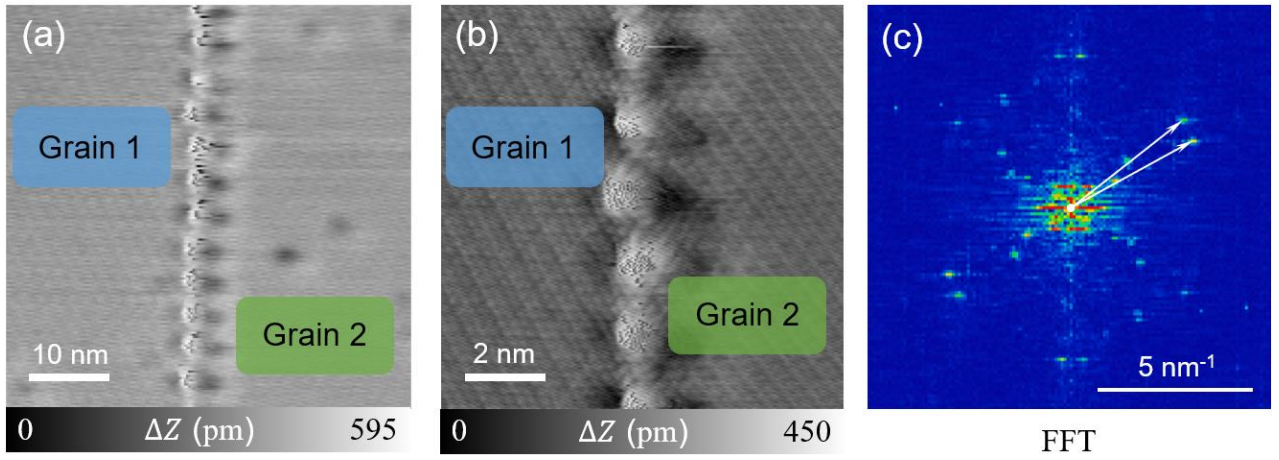


Figure S8. Characterization of a GB with misfit angle of $\theta_{\text{GB}} = 8.96 \pm 0.63^\circ$. (a) LT-STM image showing the moiré superlattices at the two grain regions. (b) High resolution LT-STM image showing the moiré and the atomic structure on both sides of the same GB. The average distance between neighboring GB protrusions is $D = 1.51 \pm 0.15$ nm. (c) The corresponding FFT map. The white arrows mark the two rotated FFT patterns associated with the atomic lattices of the two grains. Measurement parameters: $V_{\text{tip}} = 8$ mV and $I = 50$ pA.

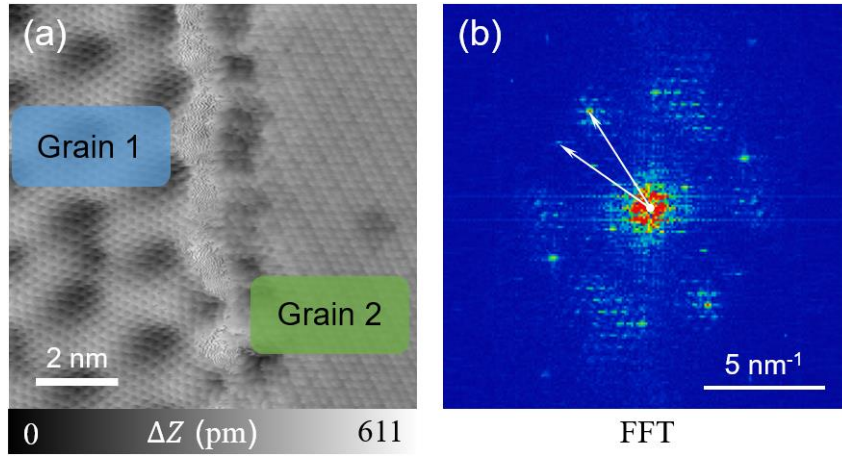


Figure S9. Characterization of a GB with misfit angle of $\theta_{\text{GB}} = 21.94 \pm 0.78^\circ$. (a) High resolution LT-STM image showing the moiré and the atomic structure on both sides of a GB. (b) The corresponding FFT map. The white arrows mark the two rotated FFT patterns associated with the atomic lattices of the two grains. Measurement parameters: $V_{\text{tip}} = 8$ mV and $I = 50$ pA.

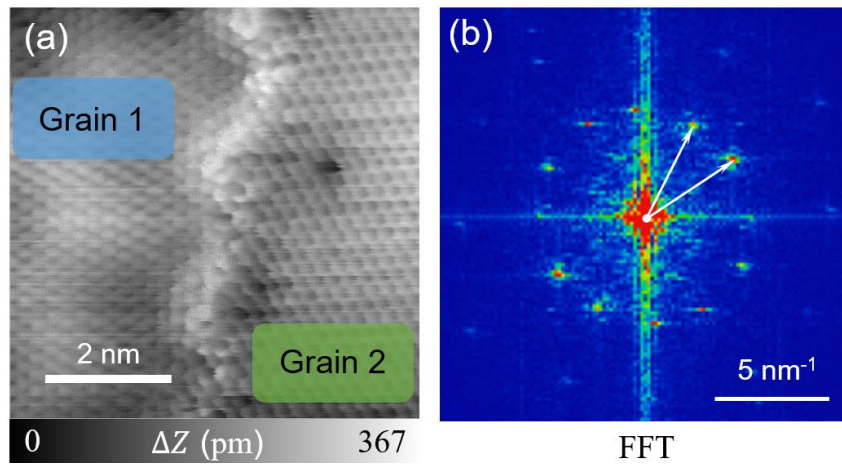


Figure S10. Characterization of a GB with misfit angle of $\theta_{\text{GB}} = 27.31 \pm 0.75^\circ$. (a) High resolution LT-STM image showing the moiré and the atomic structure on both sides of a GB. (b) The corresponding FFT map. The white arrows mark the two rotated FFT patterns associated with the atomic lattices of the two grains. Measurement parameters: $V_{\text{tip}} = 28$ mV and $I = 50$ pA.

5. Energy Dissipation Route and Average Friction Calculation

In addition to the atomic scale topography characterization, the averaged lateral force map (obtained as half of the difference between the lateral forces measured at each location during forward and backward scanning) shows higher friction patterns along at the GB region (see Fig. S11). These patterns match the topography features, indicating that the major contribution to the energy dissipation originates from the upward protrusions of corrugated graphene GB. Since these are the dominating friction contributions, the inclusion of bulk grain areas in the average friction calculation over the entire square domain presented has a minor effect on our conclusions of the GB frictional behavior.

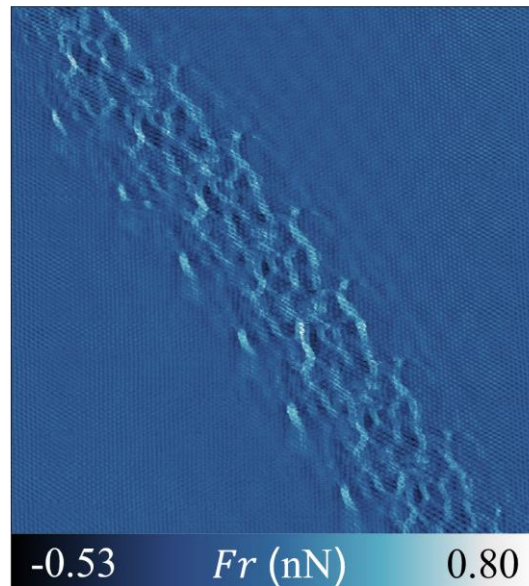


Figure S11. Averaged friction force map measured at the GB region presented in Fig. 2 of main text.

6. Reproducibility and Additional Grain Boundary Friction Measurements

In the main text, we presented results of frictional measurements on a corrugated GB of misfit angle $\theta_{GB} = 2.35 \pm 0.10^\circ$, demonstrating unconventional negative friction coefficients (NFCs) and non-monotonic velocity dependence. To verify the reproducibility of these observations, we repeated our measurements on a different corrugated GB with misfit angle of $\theta_{GB} = 14.42 \pm 0.47^\circ$ (Fig. S12a). As shown in Figs. S12b-S12d the typical lateral force loops measured at different normal loads, reveal that frictional energy dissipation emerges mainly over the GB region, showing a significant reduction with increasing normal load, similar to Fig. 2c-e of the main text. Furthermore, both the negative slope of the load dependence and the non-monotonic velocity dependence of the measured friction for this system are fully reproduced, in agreement with the results presented in Fig. 2f-g of the main text. Similar NFC behavior is observed also for a $\theta_{GB} = 1.39 \pm 0.11^\circ$ corrugated GB (see Fig. S13). Therefore, we conclude that the revealed frictional properties of corrugated GBs are of general nature and not limited to a specific system.

As a separate validation test, we present in Fig. S14 five independent measurement repetitions of the friction force velocity dependence over the $\theta_{GB} = 2.35 \pm 0.10^\circ$ corrugated GB. The results demonstrate a relatively narrow spread thus signifying the reproducibility and robustness of our GB friction measurements.

To validate that the non-monotonic velocity dependence of the friction force is associated with the negative differential friction coefficient region, we repeated those measurements for the $\theta_{GB} = 2.35 \pm 0.10^\circ$ under a normal load of 5 nN, corresponding to the plateau region in Fig. 2f. Fig. S15, demonstrates clear monotonic logarithmic increase of the friction force with sliding velocity in this region. We note that when comparing the friction force measured at a sliding velocity of 41.9 nm/s and a normal load of 5 nN to the corresponding value appearing in Fig. 2f, we obtain a somewhat lower value (by ~ 2 pN) for the former. This may be attributed to probing different GB regions in different measurements. Similar minor deviations are also observed between panels of Fig. 2f and 2g in the main text.

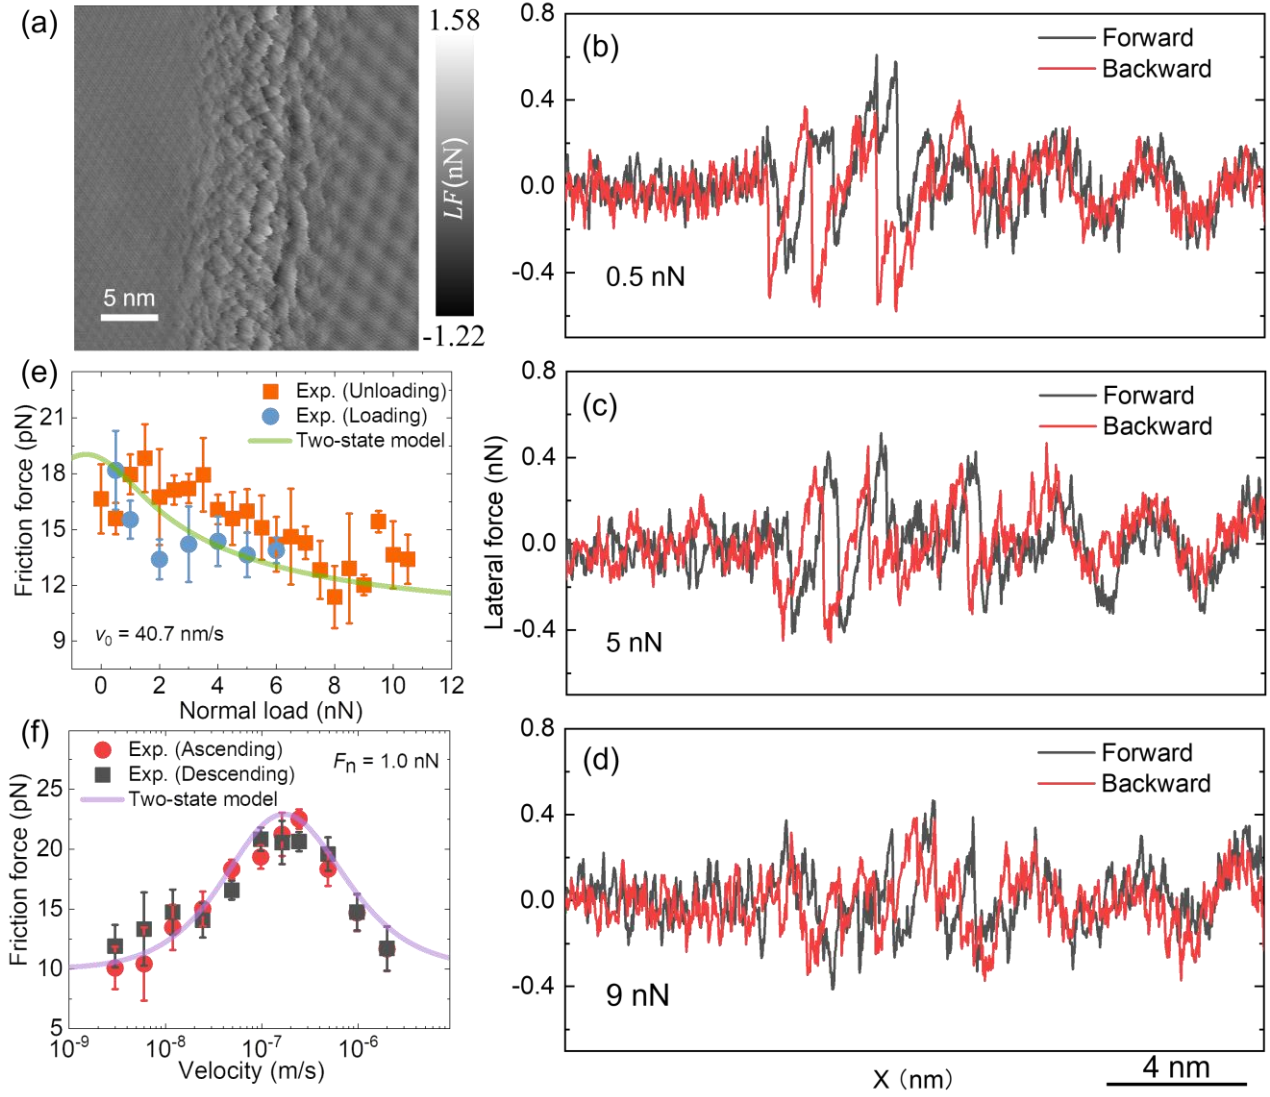


Figure S12. Frictional measurements reproducibility. (a) Lateral force map for the $\theta_{GB} = 14.42 \pm 0.47^\circ$ corrugated GB, measured under a normal load of 5.7 nN and a sliding velocity of 292.9 nm/s. (b)-(d) Forward (black) and backwards (red) lateral force traces measured under low (0.5 nN), medium (5 nN), and high (9 nN) normal loads, respectively. (e) Load and (f) velocity dependence of the measured friction force between the sliding AFM tip and the same graphene GB. Error bars represent the corresponding standard deviation obtained by performing at least 5 to 6 independent scans. The fitting parameters of the phenomenological model in panels b (green line) and c (purple line) are: $T = 300$ K, $E_1 = 0.1$ eV, $E_2 = 0.17$ eV, $\Delta x = 10.8$ Å, $\alpha = 0.1$ eV/GPa, $\beta = 0.5$, $c_0 = 0.01$ eV, $N = 2$, $k_0 = 0.032$ N/m, $f_0 = 4.88$ kHz, $F_0 = 10$ pN (see model description in the main text).

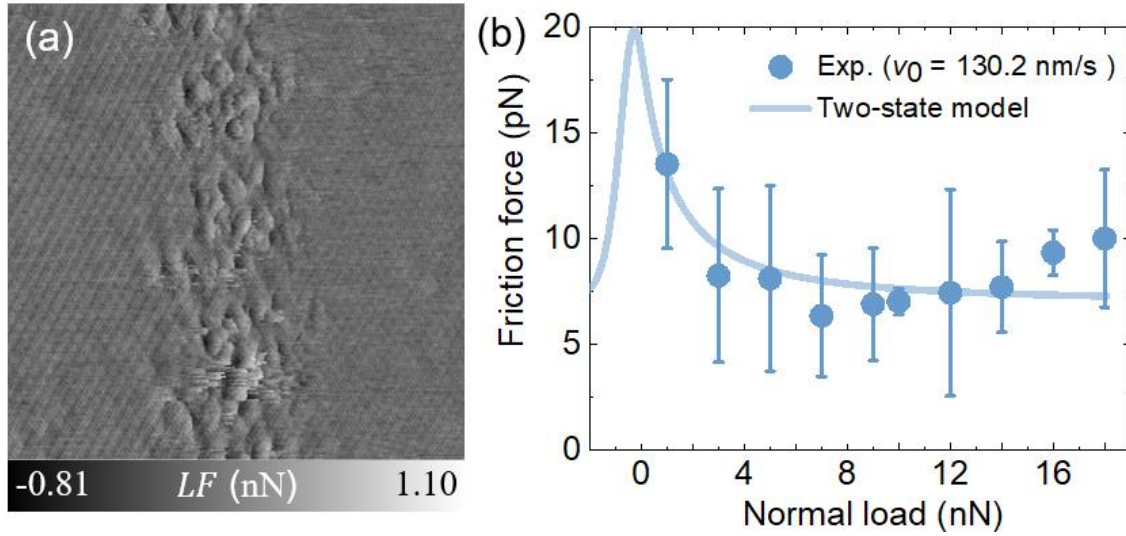


Figure S13. Frictional load dependence measurement reproducibility. (a) Lateral force map for the $\theta_{GB} = 1.39 \pm 0.11^\circ$ corrugated GB measured under a normal load of 7 nN and a sliding velocity of 130.2 nm/s. (b) Load dependence of the measured friction force between the sliding AFM tip and the same graphene GB. Error bars represent the corresponding standard deviation obtained by performing 3 independent scans. The fitting parameters of the phenomenological model in panels b (blue line) are: $T = 300$ K, $E_1 = 0.16$ eV, $E_2 = 0.26$ eV, $\Delta x = 10.8$ Å, $\alpha = 0.4$ eV/GPa, $\beta = 0.3$, $c_0 = 0.01$ eV, $N = 1$, $k_0 = 0.056$ N/m $f_0 = 39.06$ kHz, $F_0 = 7$ pN (see model description in the main text).

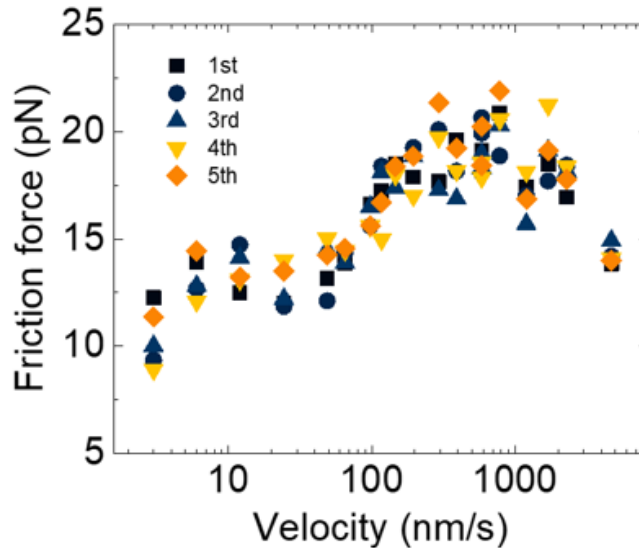


Figure S14. Frictional velocity dependence measurement reproducibility. Five independent measurement repetitions are performed on the $\theta_{GB} = 2.35 \pm 0.10^\circ$ corrugated GB. The average and standard deviation of these results are presented in Fig. 2g of the main text.

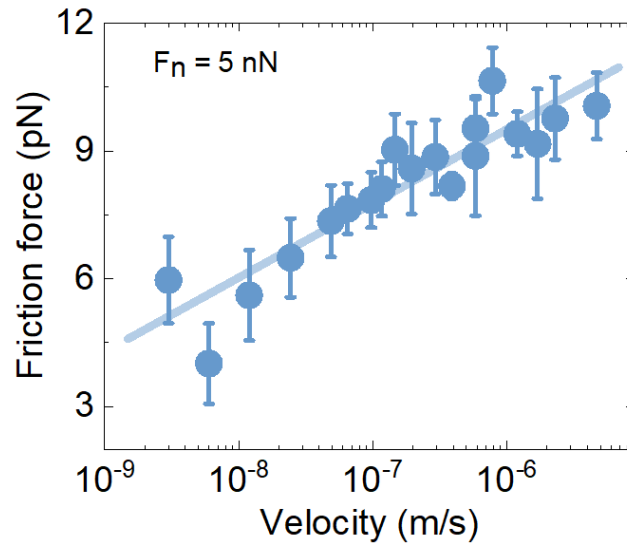


Figure S15. Velocity dependence of the measured friction force between the sliding AFM tip and the $\theta_{\text{GB}} = 2.35 \pm 0.10^\circ$ GB presented in Fig. 2 of main text under a normal load of 5 nN, corresponding to the friction plateau regime of Fig. 2f of main text. Error bars represent the corresponding standard deviation obtained by performing 5 independent scans. The solid line represents logarithmic fitting as a guide for the eye.

7. Molecular Dynamics Simulations

7.1 Simulation setup and protocol

The simulation protocol used in the present study is similar to that used in Ref. 5. The molecular dynamics (MD) simulation model system consists of a spherical-cap shaped diamond tip (2.3 nm in height, 5 nm in radius at the cut surface) sliding atop a PolyGr layer supported by a 1.36 nm thick Pt(111) substrate, as shown in Fig. S16a. Note that we use a diamond tip model rather than silicon, as used in the experiment, due to the structural simplicity of the former. Since the frictional energy dissipation mechanism of corrugated GBs relies on intrinsic protrusion buckling/unbuckling processes, the specific identity of the tip is expected to have a minor effect on the results. To rationalize the experimental results, we generate two PolyGr model systems with GB misfit angles of $\theta_{GB} = 2^\circ$ and 27.8° , matching the experimentally studied corrugated GBs. To that end, we use a Voronoi tessellation method developed by Shekhawat et al.^{6,7} The lateral dimensions of the PolyGr layers with $\theta_{GB} = 2^\circ$ and 27.8° are 29.4×28.1 and 30.0×27.7 nm², respectively. The PolyGr layers are then placed on a laterally periodic Pt(111) substrate of lateral dimensions of 41.6×40.8 nm² and thickness of 1.13 nm with the bottom layer atoms fixed at their positions, such that the left grain is aligned with the lattice direction of the Pt(111) surface, leading to moiré superstructures period of ~ 2.2 nm. Correspondingly, the superstructure periods of the right grain are ~ 2.0 nm for a GB misfit angle is $\theta_{GB} = 2^\circ$, and close to the atomic lattice period for $\theta_{GB} = 27.8^\circ$, consistent with the experimental configurations shown in Figs. 2a and 3a of the main text.

Prior to the dynamical simulations, the PolyGr/Pt(111) system is annealed at a temperature of 1,000 K, then the spherical-cap shaped diamond tip is placed on the left grain at a lateral distance of ~ 7 nm from the GB and at a height of 3.3 Å. To maintain the shape of the tip, the top two layers of the spherical-cap are kept rigid, while the rest tip atoms are unconstrained (see Fig. S16b). A dummy atom mimicking a moving stage is coupled to the center of mass of the rigid section of the tip via a lateral spring with stiffness of 10 N/m. The geometry of the combined system is then further relaxed under an external normal load (the same load used in the corresponding dynamic simulation) using the FIRE algorithm^{8,9} with a convergence force criterion of 10^{-4} eV/Å. The normal load is enforced by applying a vertical constant force on each of the atoms in the rigid section of the tip, with magnitude ranging from 0 to 0.01 nN/atom, corresponding to an overall normal load in the range of 0 to 24.4 nN.

The zero-temperature dynamic simulations are performed by driving the diamond tip with the dummy atom moving at a constant velocity of $v_0 = 2$ m/s along the x lateral direction. To remove

the generated heat, viscous velocity damping with a damping coefficient of $\eta = 1.0 \text{ ps}^{-1}$ is applied to flexible regions of the tip and the Pt(111) substrate far away from the sliding interface (see Figure S16b). To that end, damping forces $\mathbf{f}_{\text{damp,tip}}^i(t)$ and $\mathbf{f}_{\text{damp,Pt}}^i(t)$ are applied to each atom, i , within the damped regions in the tip and the Pt substrate, respectively, via:

$$\begin{cases} \mathbf{f}_{\text{damp,tip}}^i(t) = -m_{\text{C}}\eta(v_x^i(t) - v_0)\hat{\mathbf{x}} - m_{\text{C}}\eta v_y^i(t)\hat{\mathbf{y}} - m_{\text{C}}\eta v_z^i(t)\hat{\mathbf{z}} \\ \mathbf{f}_{\text{damp,Pt}}^i(t) = -m_{\text{Pt}}\sum_{\alpha=x,y,z}\eta v_{\alpha}^i(t)\hat{\boldsymbol{\alpha}} \end{cases} \quad (\text{S2})$$

Here, m_{C} and m_{Pt} are the atomic masses of carbon and Pt, respectively, $v_{\alpha}^i(t)$ is the α Cartesian velocity component of the damped i^{th} atom at time t , and $\hat{\boldsymbol{\alpha}} = \hat{\mathbf{x}}, \hat{\mathbf{y}}, \hat{\mathbf{z}}$ are unit vectors along the Cartesian x , y and z directions, respectively. Note that the damping in the sliding (x) direction in the tip is applied to the relative velocity with respect to the moving stage, accounting for the fact that in realistic scenarios viscous dissipation is caused by the internal degrees of freedom of the sheared bodies. We verify that our choice of damping coefficient has minor effect on the dynamics at the shear interface.²

To prevent global sliding and/or rotation of the PolyGr layer due to the tip motion, two ribbons of outskirt carbon atoms at the two parallel sides in the PolyGr layer (see stripes regions in Fig. S16) are constrained to their initial position via lateral springs of stiffness 0.176 N/m. For each normal load and GB angle, the dynamic simulation last for 7 ns, which allows us to eliminate initial transient effects. The lateral force traces are obtained by recording the instantaneous spring force exerted on the dummy atom along the sliding direction and inverting its sign. The average friction force is calculated by averaging the forward and backward force traces over distances of 6.5 and 6 nm, spanning the $\theta_{\text{GB}} = 2^\circ$ and 27.8° GBs, respectively, as shown in Fig. S17.

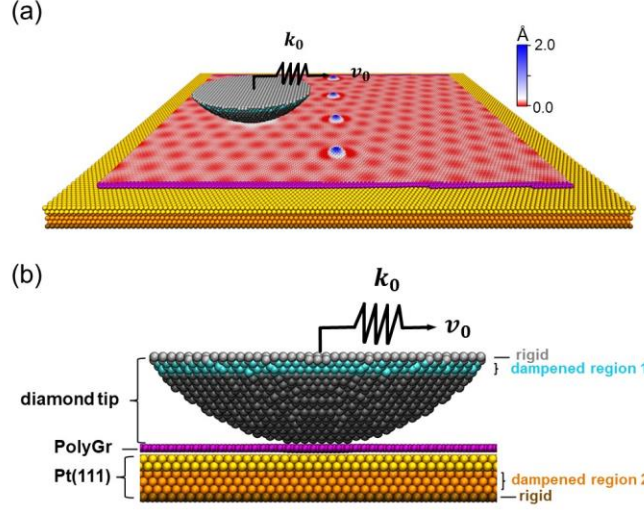


Figure S16. MD simulation setup. (a) Perspective view of the simulation model system with $\theta_{GB} = 2^\circ$. (b) Side view of the tip region presented in panel (a). Brown, orange, and yellow spheres in the substrate region represent rigid, dampened, and flexible Pt atoms. Light-gray, cyan, and dark-gray spheres in the tip region represent rigid, dampened, and flexible carbon atoms. The unconstrained graphene layer atoms are color coded according to their out-of-plane corrugation (see color bar in panel (a)), and the constrained graphene atoms are represented by purple spheres.

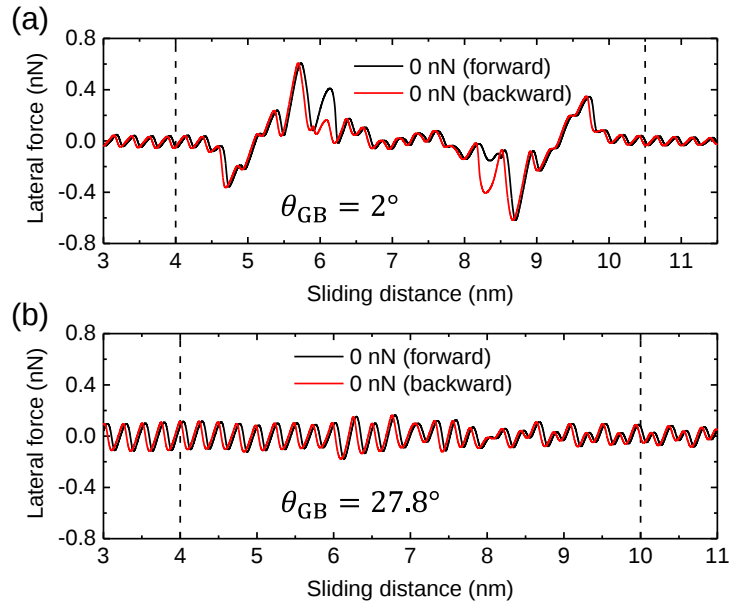


Figure S17. Lateral forward (black) and backward (red) force traces as a function of sliding distance over the (a) $\theta_{GB} = 2^\circ$ and (b) $\theta_{GB} = 27.8^\circ$ GBs under zero normal load. The region between the dashed vertical lines is used to calculate the average friction force.

7.2 Additional simulation results

Complementary to the simulation trajectories shown in Fig. 4e of the main text, we present in Fig. S18 additional trajectories of atomic height and vertical velocity for a chosen atom at a dislocation of a $\theta_{GB} = 2^\circ$ GB. The results demonstrate that as normal load increases, the instantaneous buckling velocity decreases until the trajectories become smooth. Consequently, the buckling induced energy dissipation reduces with increasing normal load.

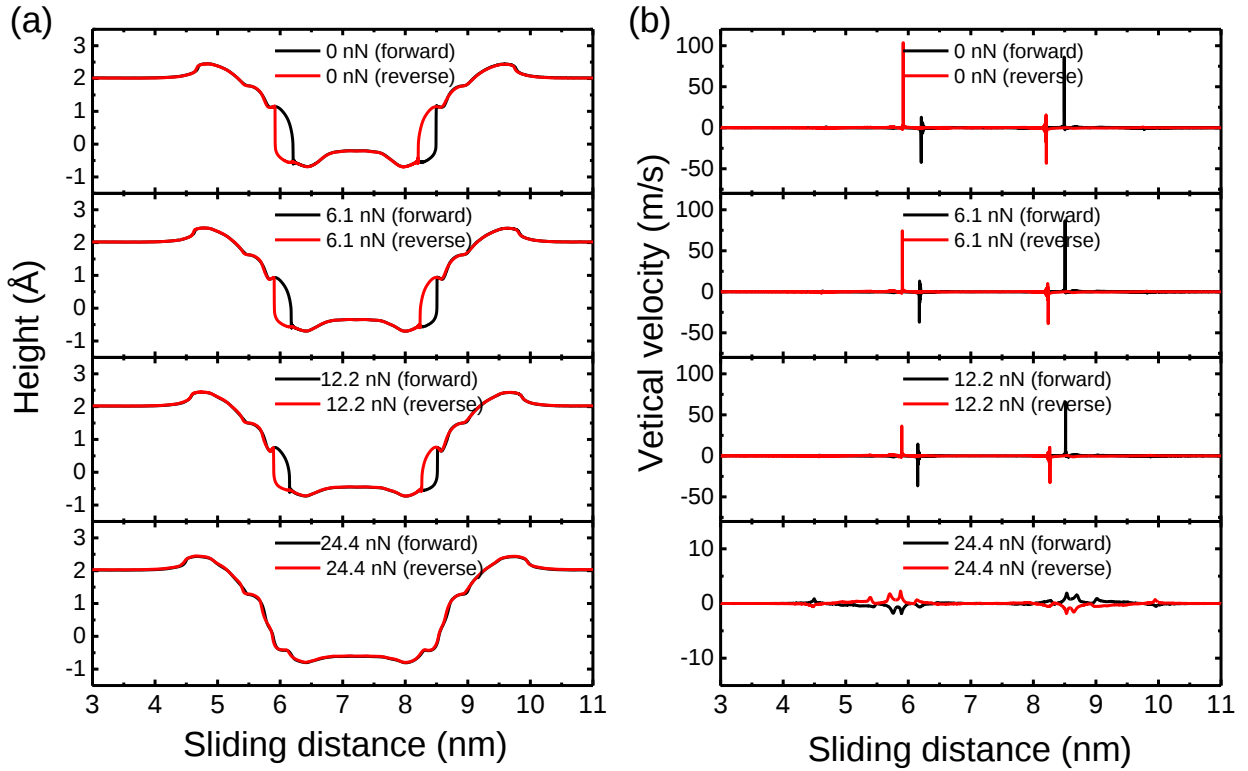


Figure S18. Additional simulation trajectories of (a) atomic height and (b) vertical velocity, under different normal loads, of an atom residing at a dislocation of a $\theta_{GB} = 2^\circ$ GB.

7.3 Simulation parameters for carbon-Pt interactions

In view of the lack of anisotropic potentials for carbon-Pt interactions, we use the Lennard-Jones (LJ) potential, which was shown to provide satisfactory qualitative interpretation of complex frictional mechanisms of graphene on various substrates.^{5,10-12} Our choice of LJ parameters is primarily based on benchmarking the binding energy ΔE_b and equilibrium distance d against available experimental and computational (using density functional theory (DFT)) reference data. Experimental and DFT data for the graphene/Pt(111) interface are summarized in Table S1, along

with previous structural relaxation results based on the LJ potential. Most previous DFT calculations predict adsorption energies in the range of $\Delta E_b = 30 - 90$ meV/C,¹³⁻¹⁶ and equilibrium distances of 3.1-3.8 Å. Experimental data suggest an equilibrium graphene/Pt(111) distance of 3.3 Å.¹⁷

We note that several studies using the LJ potential for the graphene/Pt interface overestimated the binding energy and underestimated the equilibrium distance with respect to DFT and experimental reference data.^{18,19} Moseler et al.¹⁰ used the following set of LJ parameters: $\varepsilon_{C-Pt} = 0.011236$ eV and $\sigma_{C-Pt} = 3.408$ Å, fitted against the DFT reference of $\Delta E_b = 68$ meV/C¹⁴ and the experimental reference of $d = 3.3$ Å¹⁷ with a LJ cutoff distance of $R_{cut} = 6$ Å. The latter, however, may be too small to fully capture long-range van der Waals contributions. Hence, in the present study, we adopt the following alternative set of parameters: $\varepsilon_{C-Pt} = 0.006$ eV and $\sigma_{C-Pt} = 3.35$ Å with a LJ cutoff distance $R_{cut} = 12$ Å. This parameterization provides a binding energy of $\Delta E_b = 48.4$ meV/C and an equilibrium distance $d = 3.3$ Å, in good agreement with vdW-DF and vdW-DF2 results^{14,16} and the experimental equilibrium distance.¹⁷ Furthermore, the moiré superstructure periodicity and corrugation obtained using this force-field (see Figs. 4a-b of the main text) are compatible with our experimental results and with previous experimental observations.¹⁵ This supports the suitability of our LJ potential parameterization for studying the frictional behavior of PolyGr layers deposited atop the Pt(111) surface.

Table S1. Binding energies (ΔE_b) and equilibrium distances (d) obtained for the graphene/Pt(111) interface via DFT and classical Lennard-Jones force-field calculations. For the latter, the corresponding potential parameters are provided. An available experimental result for the graphene/Pt(111) equilibrium distance is provided for comparison.

Reference	ε_{C-Pt} (eV)	σ_{C-Pt} (Å)	ΔE_b (meV/C)	d (Å)	R_{cut} (Å)	method
Khomyakov et al. (2009) ¹³			38	3.3		DFT(LDA)
Hamada & Otani (2010) ¹⁴			52	3.8		DFT(vdW-DF)
			54	3.71		DFT(vdW-DF2)
			89	3.17		DFT(vdW-DF ^{C09x})
			68	3.24		DFT(vdW-DF2 ^{C09x})
Gao et al. (2011) ¹⁵			38.6-39.8	>3.1		DFT
Martínez et al.(2016) ²⁰			240-290	3.13-3.23		DFT(rPBE+D)
Mortensen et al. (2010) ¹⁶			43	3.67		DFT(vdW-DF)
			33	3.25		DFT(LDA)
Sutter et al. (2009) ¹⁷				3.3		Exp.
Morrow & Striolo (2007) ¹⁸	0.02206	2.95	128	2.91	9	MD
Mi et al. (2020) ¹⁹	0.4092	2.936	237	3.05 (2.894) ^a	9	MD
Moseler et al. (2014) ¹⁰	0.011236	3.408	68 (66) ^a	3.3 (3.408) ^a	6	MD
			(88) ^a	(3.36) ^a	9	
			(94) ^a	(3.354) ^a	12	
This study	0.006	3.35	48.4	3.3	12	MD

^a The values in parentheses are results of our calculations obtained using the LJ parameters provided in the cited studies with various R_{cut} values, as detailed in the table.

References:

- 1 Meyer, E., Bennewitz, R. & Hug, H. J. *Scanning Probe Microscopy: The Lab on a Tip* Graduate Texts in Physics, (Springer Cham, 2021).
- 2 Gao, X., Ouyang, W., Hod, O. & Urbakh, M. Mechanisms of frictional energy dissipation at graphene grain boundaries. *Phys. Rev. B* **103**, 045418 (2021).
- 3 Anderson, P. M., Hirth, J. P. & Lothe, J. *Theory of dislocations*, (Cambridge University Press, 2017).
- 4 Yazyev, O. V. & Louie, S. G. Topological defects in graphene: Dislocations and grain boundaries. *Phys. Rev. B* **81**, 195420 (2010).
- 5 Song, Y., Gao, X., Hinaut, A., Scherb, S., Huang, S., Glatzel, T., Hod, O., Urbakh, M. & Meyer, E. Velocity Dependence of Moiré Friction. *Nano Lett.* **22**, 9529-9536 (2022).
- 6 Ophus, C., Shekhawat, A., Rasool, H. & Zettl, A. Large-scale experimental and theoretical study of graphene grain boundary structures. *Phys. Rev. B* **92**, 205402 (2015).
- 7 Shekhawat, A. & Ritchie, R. O. Toughness and strength of nanocrystalline graphene. *Nat. Commun.* **7**, 10546 (2016).
- 8 Bitzek, E., Koskinen, P., Gähler, F., Moseler, M. & Gumbsch, P. Structural Relaxation Made Simple. *Phys. Rev. Lett.* **97**, 170201 (2006).
- 9 Guénolé, J., Nöhring, W. G., Vaid, A., Houllé, F., Xie, Z., Prakash, A. & Bitzek, E. Assessment and optimization of the fast inertial relaxation engine (fire) for energy minimization in atomistic simulations and its implementation in lammmps. *Comput. Mater. Sci.* **175**, 109584 (2020).
- 10 Klemenz, A., Pastewka, L., Balakrishna, S. G., Caron, A., Bennewitz, R. & Moseler, M. Atomic Scale Mechanisms of Friction Reduction and Wear Protection by Graphene. *Nano Lett.* **14**, 7145-7152 (2014).
- 11 Liu, Z., Vilhena, J. G., Hinaut, A., Scherb, S., Luo, F., Zhang, J., Glatzel, T., Gnecco, E. & Meyer, E. Moire-Tile Manipulation-Induced Friction Switch of Graphene on a Platinum Surface. *Nano Lett.* **23**, 4693-4697 (2023).
- 12 Li, S., Li, Q., Carpick, R. W., Gumbsch, P., Liu, X. Z., Ding, X., Sun, J. & Li, J. The evolving quality of frictional contact with graphene. *Nature* **539**, 541-545 (2016).
- 13 Khomyakov, P. A., Giovannetti, G., Rusu, P. C., Brocks, G., van den Brink, J. & Kelly, P. J. First-principles study of the interaction and charge transfer between graphene and metals. *Phys. Rev. B* **79**, 195425 (2009).
- 14 Hamada, I. & Otani, M. Comparative van der Waals density-functional study of graphene on metal surfaces. *Phys. Rev. B* **82**, 153412 (2010).
- 15 Gao, M., Pan, Y., Huang, L., Hu, H., Zhang, L. Z., Guo, H. M., Du, S. X. & Gao, H. J. Epitaxial growth and structural property of graphene on Pt(111). *Appl. Phys. Lett.* **98**, 033101 (2011).
- 16 Vanin, M., Mortensen, J. J., Kelkkanen, A. K., Garcia-Lastra, J. M., Thygesen, K. S. & Jacobsen, K. W. Graphene on metals: A van der Waals density functional study. *Phys. Rev. B* **81**, 081408 (2010).
- 17 Sutter, P., Sadowski, J. T. & Sutter, E. Graphene on Pt(111): Growth and substrate interaction. *Phys. Rev. B* **80**, 245411 (2009).
- 18 Morrow, B. H. & Striolo, A. Morphology and Diffusion Mechanism of Platinum Nanoparticles on Carbon Nanotube Bundles. *J. Phys. Chem. C* **111**, 17905-17913 (2007).

- 19 Sun, B., Ouyang, W., Gu, J., Wang, C., Wang, J. & Mi, L. Formation of Moiré superstructure of epitaxial graphene on Pt(111): A molecular dynamic simulation investigation. *Mater. Chem. Phys.* **253**, 123126 (2020).
- 20 Martínez, J. I., Merino, P., Pinardi, A. L., Gonzalo, O.-I., López, M. F., Méndez, J. & Martín-Gago, J. A. Role of the Pinning Points in epitaxial Graphene Moiré Superstructures on the Pt(111) Surface. *Sci. Rep.* **6**, 20354 (2016).